



BSI Standards Publication

Welding — Arc-welded joints in aluminium and its alloys — Quality levels for imperfections

National foreword

This British Standard is the UK implementation of EN ISO 10042:2018. It is identical to ISO 10042:2018. It supersedes BS EN ISO 10042:2005, which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee WEE/36, Qualification of welding personnel and welding procedures.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2018
Published by BSI Standards Limited 2018

ISBN 978 0 580 94837 4

ICS 25.160.40

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 July 2018.

Amendments/corrigenda issued since publication

Date	Text affected
<hr/>	

English Version

Welding — Arc-welded joints in aluminium and
its alloys — Quality levels for imperfections
(ISO 10042:2018)

Soudage — Assemblages en aluminium et alliages
d'aluminium soudés à l'arc — Niveaux de qualité
par rapport aux défauts (ISO 10042:2018)

Schweißen — Lichtbogenschweißverbindungen
an Aluminium und seinen
Legierungen — Bewertungsgruppen von
Unregelmäßigkeiten (ISO 10042:2018)

This European Standard was approved by CEN on 10 June 2018.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the CEN-CENELEC Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the CEN-CENELEC Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

CEN-CENELEC Management Centre: Avenue Marnix 17, B-1000 Brussels

European foreword

This document (EN ISO 10042:2018) has been prepared by Technical Committee ISO/TC 44 "Welding and allied processes" in collaboration with Technical Committee CEN/TC 121 "Welding and allied processes" the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by January 2019, and conflicting national standards shall be withdrawn at the latest by January 2019.

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. CEN shall not be held responsible for identifying any or all such patent rights.

This document supersedes EN ISO 10042:2005.

According to the CEN-CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Bulgaria, Croatia, Cyprus, Czech Republic, Denmark, Estonia, Finland, Former Yugoslav Republic of Macedonia, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Latvia, Lithuania, Luxembourg, Malta, Netherlands, Norway, Poland, Portugal, Romania, Serbia, Slovakia, Slovenia, Spain, Sweden, Switzerland, Turkey and the United Kingdom.

Endorsement notice

The text of ISO 10042:2018 has been approved by CEN as EN ISO 10042:2018 without any modification.

Contents		Page
Foreword		iv
Introduction		vi
1	Scope	1
2	Normative references	1
3	Terms and definitions	1
4	Symbols	2
5	Assessment of imperfections	3
Annex A (informative) Examples of the determination of the percent porosity		16
Annex B (informative) Additional information and guidelines for users of this document		18
Bibliography		19

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 44, *Welding and allied processes*, Subcommittee SC 10, *Quality management in the field of welding*.

This third edition cancels and replaces the second edition ([ISO 10042:2005](http://www.iso.org/iso/10042:2005)), of which it constitutes a minor revision. The changes compared to the previous edition are as follows:

- reference numbers from [ISO 4063](http://www.iso.org/iso/4063) have been deleted in the Scope;
- in [Table 1](#), 1.3, reference number [ISO 6520-1](http://www.iso.org/iso/6520-1) has been changed from “2012 - uniformly distributed porosity” to “2018 - surface porosity”;
- in [Table 1](#), 1.8, a new figure has been inserted and changes to quality levels B and C have been made;
- in [Table 1](#), 1.9, changes to quality level C have been made;
- in [Table 1](#), 1.14, a drawing has been added;
- in [Table 1](#), 1.15, changes to quality level D have been made;
- in [Table 1](#), 1.18, a drawing has been deleted and a new one inserted, and reference to 6520-1-5013 “shrinkage groove” has been deleted;
- in [Table 1](#), 1.19 to 1.21, imperfections have been added with values from [ISO 5817](http://www.iso.org/iso/5817): poor restart, stray arc, spatter;
- in [Table 1](#), 2.2, changes to quality levels B and C have been made;
- in [Table 1](#), 2.10, changes to quality levels C and D have been made;
- in [Table 1](#), 2.11, a drawing has been deleted and new ones introduced, requirements for “Butt joint (full penetration)” have been updated;
- in [Table 1](#), 2.12, a new drawing has been introduced with new requirements, and changes to quality levels C and D have been made;

— editorial changes have been made.

Requests for official interpretation of any aspect of this document should be directed to the secretariat of ISO/TC 44/SC 10 via your national standards body. A complete listing of these bodies can be found at www.iso.org.

Introduction

This document is intended to be used as a reference in drafting application codes and/or other application standards. It contains a simplified selection of arc welding imperfections based on the designations given in [ISO 6520-1](#).

Some imperfections described in [ISO 6520-1](#) have been used directly while others have been grouped together. The basic numerical referencing system from [ISO 6520-1](#) has been used.

The purpose of this document is to define the dimensions of typical imperfections which can be expected in normal fabrication. It can be used within a quality system for the production of welded joints. It provides three sets of dimensional values from which a selection can be made for a particular application. The quality level necessary in each case needs to be defined by the application standard or the responsible designer, in conjunction with the manufacturer, user and/or other parties concerned. The quality level are prescribed before the start of production, preferably at the enquiry or order stage. For special purposes, additional details can be necessary.

The quality levels given in this document provide basic reference data and are not specifically related to any particular application. They refer to the types of welded joint in fabrication and not to the complete product or component itself. It is possible, therefore, that different quality levels are applied to individual welded joints in the same product or component.

It is normally be expected that, for a particular welded joint, the dimensional limits for imperfections can all be covered by specifying one quality level. In some cases, it can be necessary to specify different quality levels for different imperfections in the same welded joint.

The choice of quality level for any application takes account of design considerations, subsequent processing (e.g. surfacing), mode of stressing (e.g. static, dynamic), service conditions (e.g. temperature, environment) and consequences of failure. Economic factors are also important and include not only the cost of welding but also of inspection, test and repair.

Although this document includes types of imperfection relevant to the arc welding processes given in [Clause 1](#), only those which are applicable to the process and application in question are considered.

Imperfections are quoted in terms of their actual dimensions, and their detection and evaluation can require the use of one or more methods of non-destructive testing. The detection and sizing of imperfections is dependent on the testing methods and the extent of testing specified in the application standard or contract.

This document does not address the methods used for the detection of imperfections. However, [ISO 17635](#) contains a correlation between the quality level and acceptance level for different NDT (non-destructive testing) methods.

This document is directly applicable to visual testing of welds and does not include details of recommended methods of detection or sizing by other non-destructive means. There are difficulties in using these limits to establish appropriate criteria applicable to NDT methods such as ultrasonic (UT), radiographic (RT) and penetrant testing (PT), for which additional requirements for testing can be necessary.

The values given for imperfections are for welds produced using normal welding practice. Requirements for smaller (more stringent) values as stated in quality level B can include additional manufacturing processes, e.g. grinding, TIG dressing.

Welding — Arc-welded joints in aluminium and its alloys — Quality levels for imperfections

1 Scope

This document specifies quality levels for imperfections in arc-welded joints in aluminium and its alloys. It applies to material thicknesses above 0,5 mm.

Three quality levels are given in order to permit application to a wide range of welded constructions. They are designated by symbols B, C and D. Quality level B corresponds to the highest requirement on the finished weld. The quality levels refer to production quality and not to the fitness for purpose (see 3.2) of the product manufactured.

This document is applicable to all types of welds (e.g. butt welds, fillet welds and branch connections), to manual, mechanized and automated welding, and to all welding positions.

It is applicable to the following welding processes:

- metal inert gas welding (MIG welding); gas metal arc welding /USA;
- tungsten inert gas welding (TIG welding); gas tungsten arc welding /USA;
- plasma arc welding.

It is not applicable to metallurgical aspects (e.g. grain size, hardness).

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

ISO 6520-1, Welding and allied processes — Classification of geometric imperfections in metallic materials — Part 1: Fusion welding

3 Terms and definitions

For the purposes of this document, the following terms and definitions apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

3.1

quality level

description of the quality of a weld on the basis of type, size and amount of selected imperfections

3.2

fitness for purpose

ability of a product, process or service to serve a defined purpose under specific conditions

3.3
short imperfection

<welds of length ≥ 100 mm> imperfection whose total length is not greater than 25 mm in any 100 mm of their length

3.4
short imperfection

<welds less than 100 mm long> imperfection whose total length is not greater than 25 % of the length of the weld

3.5
systematic imperfection

imperfection that is repeatedly distributed in the weld over the weld length to be examined, the size of each individual imperfection being within the specified limits


3.6
cross-sectional area

area to be considered after fracture or sectioning

3.7
projected area

area where imperfections distributed along the volume of the weld under consideration are imaged two-dimensionally

Note 1 to entry: In contrast to the *cross-sectional area* (3.6), the occurrence of imperfections is dependent on the weld thickness when exposed radiographically (see Figure 1).

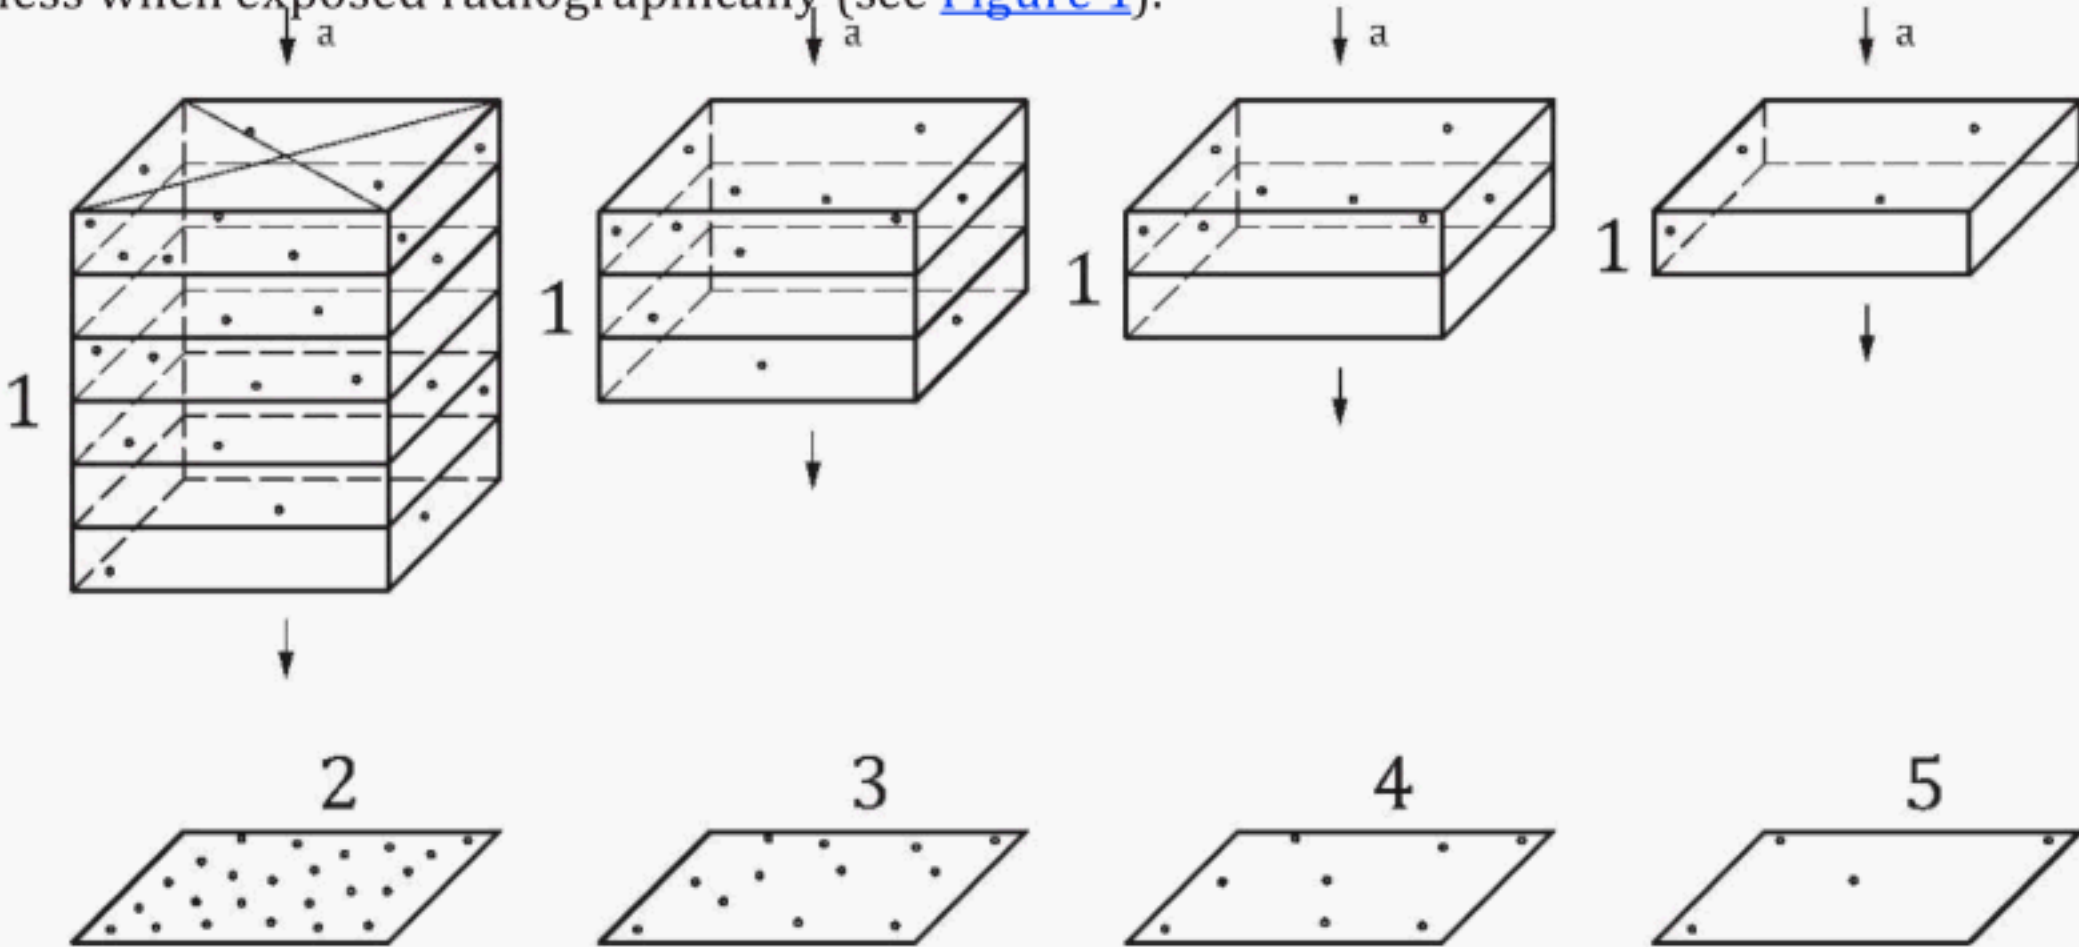

Key	
1	4 pores per volume unit
2	6-fold thickness
3	3-fold thickness
4	2-fold thickness
5	1-fold thickness
a	Direction of X-rays.

Figure 1 — Radiographic films of specimens with identical occurrence of pores per volume unit

4 Symbols

The following symbols are used in Table 1.

- A area of clustered porosity
- a nominal throat thickness of a fillet weld (see also ISO 2553)

b	width of the weld
d	diameter of a gas pore
d_A	diameter of area surrounding a area of clustered porosity
d_{Ac}	diameter of circle surrounding total gas pore area
h	height or width of an imperfection
l	length of imperfection in longitudinal direction of weld
l_p	length of projected or cross-sectional area
s	nominal butt weld thickness (see also ISO 2553)
t	wall or plate thickness (nominal size)
w_p	width or height of cross-sectional area
z	leg length of a fillet weld (see also ISO 2553)

5 Assessment of imperfections

Limits on imperfections are given in [Table 1](#).

Systematic imperfections are only permitted in quality level D, provided other requirements of [Table 1](#) are fulfilled.

A welded joint should usually be assessed for each individual type of imperfection separately (see [Table 1](#), 1.1 to 3.2).

Different types of imperfection occurring at any cross-section of the joint need special consideration (see multiple imperfections in [Table 1](#), 4.1).

The limits on multiple imperfections (see [Table 1](#)) are only applicable in cases where the requirements for a single imperfection are not exceeded.

Any two adjacent imperfections separated by a distance smaller than the major dimension of the smaller imperfection shall be considered as a single imperfection.

Table 1 — Limits on imperfections

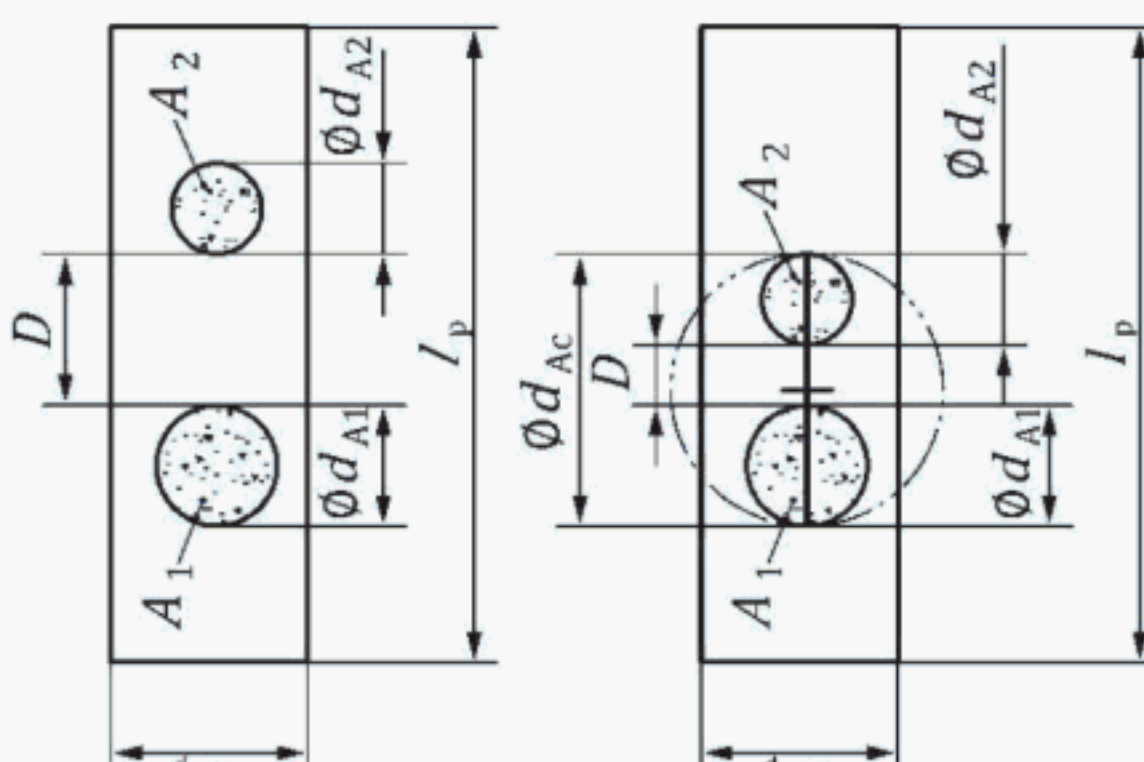
No.	Reference No. in ISO 6520-1	Designation of imperfection	Remarks	t mm	Limits on imperfections for quality levels		
1 Surface imperfections							
1.1	100	Crack	—	≥0,5	Not permitted	Not permitted	
1.2	104	Crater crack	—	≥0,5	$h \leq 0,4s$ or $0,4a$ $l \leq 0,4s$ or $0,4a$	Not permitted	
1.3	2018	Surface porosity	For the assessment of the porosity, see examples given in Annex A .	≥0,5	≤2 %	≤1 %	
1.4	2013	Clustered (localized) porosity					

Table 1 (continued)

No.	Reference No. in ISO 6520-1	Designation of imperfection	Remarks	t mm	Limits on imperfections for quality levels	B
			Reference length for l_p is 100 mm. The total gas pore area within the cluster is represented by a circle of diameter, d_A , surrounding all the gas pores. The requirements for a single gas pore shall be met by all the gas pores within this circle. A permitted porous area shall be local. The possibility of the pore cluster masking other imperfections shall be taken into consideration. If D is less than d_{A1} or d_{A2} , whichever is smaller, then the total gas pore area is represented by a circle of diameter, d_{Ac} , where $d_{Ac} = d_{A1} + d_{A2} + D$. Systematic clustered porosity is not permitted.	≥0,5	$d_A \leq 25$ mm or $d_{A,max} \leq w_p$ d_A corresponds to d_{A1} , d_{A2} or d_{Ac} whichever is applicable	Not permitted
1.5	2014	Linear porosity	—	≥0,5	Not permitted	Not permitted
1.6	2017	Surface pore	Maximum dimension of a single gas pore:	0,5 to 3 >3	$d \leq 0,3s$ or $0,3a$ $d \leq 0,4s$ or $0,4a$ max. 3 mm	$d \leq 0,1s$ or $0,1a$ $d \leq 0,2s$ or $0,2a$ max. 1 mm
1.7	2025	End crater pipe	—	≥0,5	$h \leq 0,4t$ max. 3 mm	Not permitted
1.8	401	Lack of fusion (incomplete fusion)	—	≥0,5	Short imperfections $h \leq 0,1s$ or $0,1a$ max. 3 mm	Not permitted

Table 1 (continued)

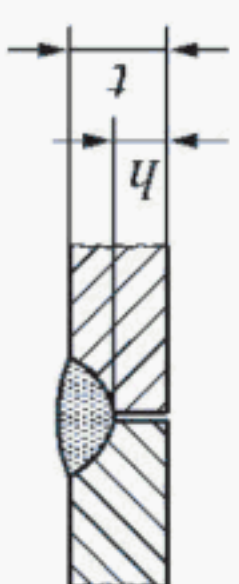
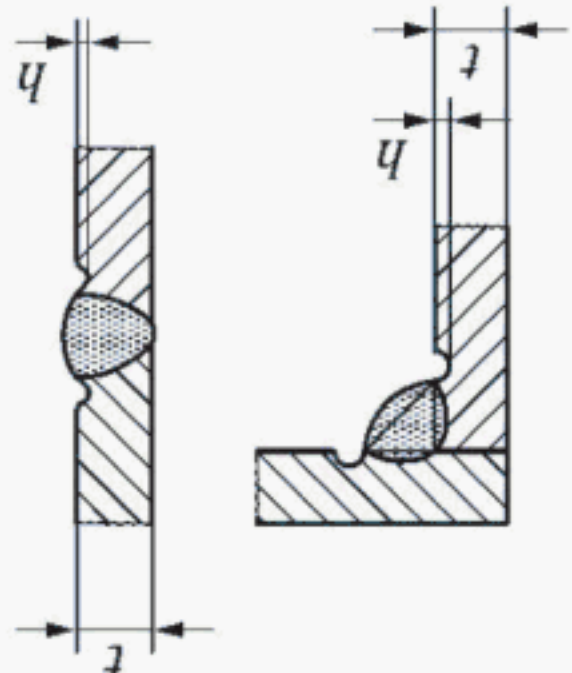
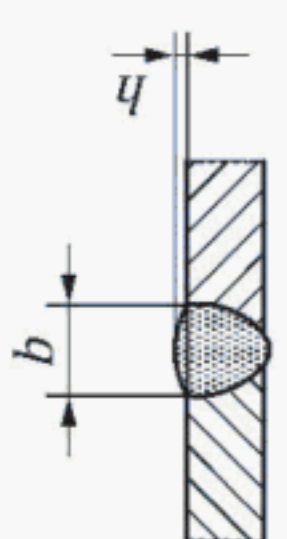
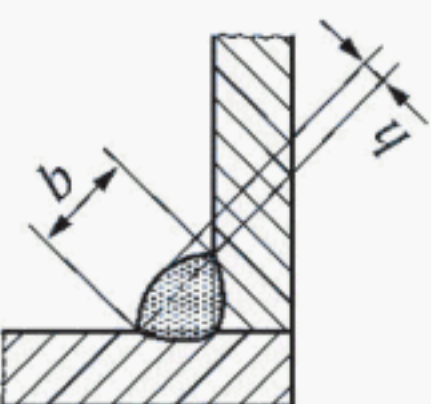
No.	Reference No. in ISO 6520-1	Designation of imperfection	Remarks	t mm	Limits on imperfections for quality levels	B
1.9	4021	Incomplete root penetration		$\geq 0,5$	Short imperfections but no systematic imperfections. $h \leq 0,2t$ max. 2 mm	Not permitted
1.10	5011	Continuous undercut		0,5 to 3 >3	$h \leq 0,2t$ $h \leq 0,2t$ but max. 1 mm	Not permitted Not permitted
	5012	Intermittent undercut (short imperfection)	Smooth transition required. 5012 is not regarded as a systematic imperfection.	0,5 to 3 >3	$h \leq 0,2t$ $h \leq 0,2t$ but max. 1,5 mm	$h \leq 0,1t$ $h \leq 0,1t$ but max. 0,5 mm
1.11	502	Excess weld metal	Smooth transition required. 	$\geq 0,5$	$h \leq 1,5 \text{ mm } 0,2b$ max. 10 mm	$h \leq 1,5 \text{ mm } + 0,1b$ max. 6 mm
1.12	503	Excessive convexity		$\geq 0,5$	$h \leq 1,5 \text{ mm } + 0,3b$ max. 5 mm	$h \leq 1,5 \text{ mm } + 0,1b$ max. 3 mm

Table 1 (continued)

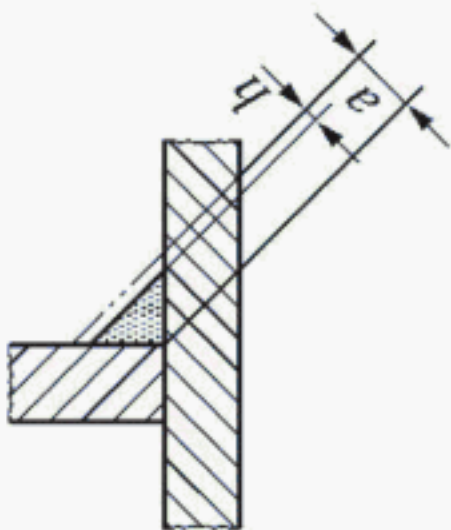
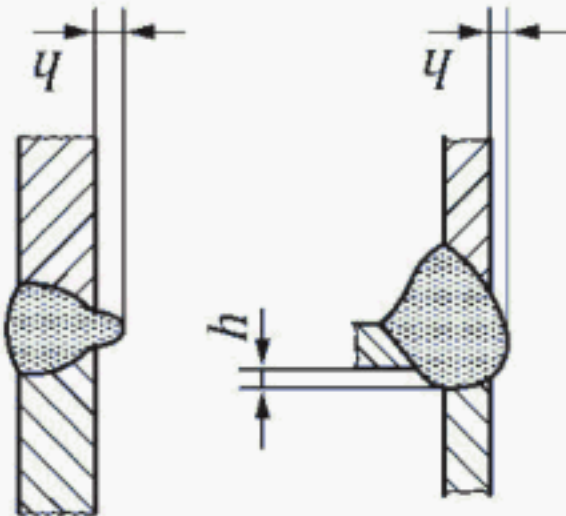
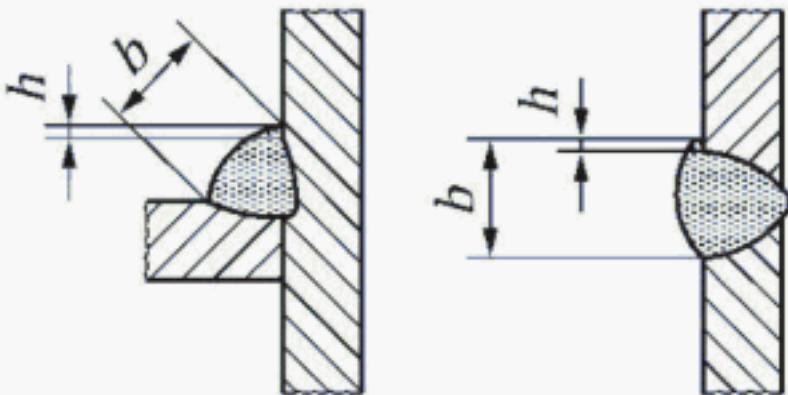
No.	Reference No. in ISO 6520-1	Designation of imperfection	Remarks	t mm	Limits on imperfections for quality levels		
					D	C	B
1.13	5213	Insufficient throat thickness	Not applicable to processes proven to give greater depth of penetration. 	≥0,5	$h \leq 0,3a$ max. 2 mm	$h \leq 0,2a$ max. 1,5 mm	$h \leq 0,1a$ max. 1 mm
1.14	504	Excess penetration		≥0,5	$h \leq 6$ mm	$h \leq 4$ mm	$h \leq 3$ mm
1.15	506	Overlap		≥0,5	Short imperfections permitted, but $h \leq 0,2b$	Not permitted	Not permitted

Table 1 (continued)

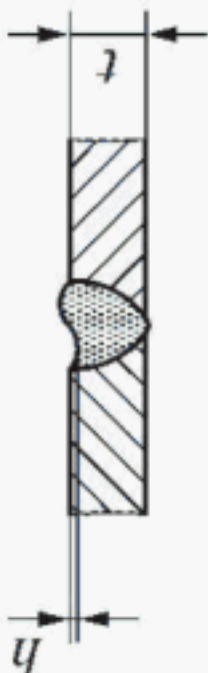
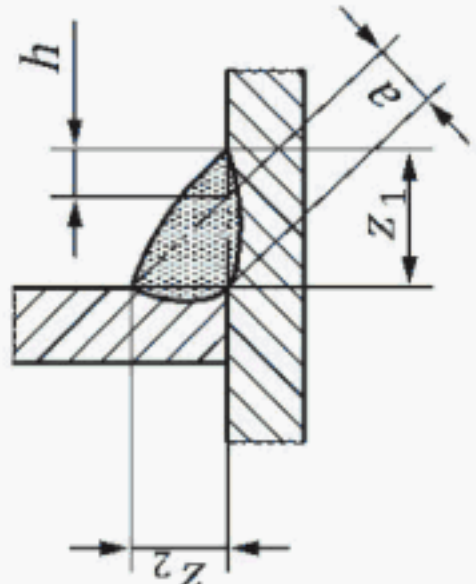
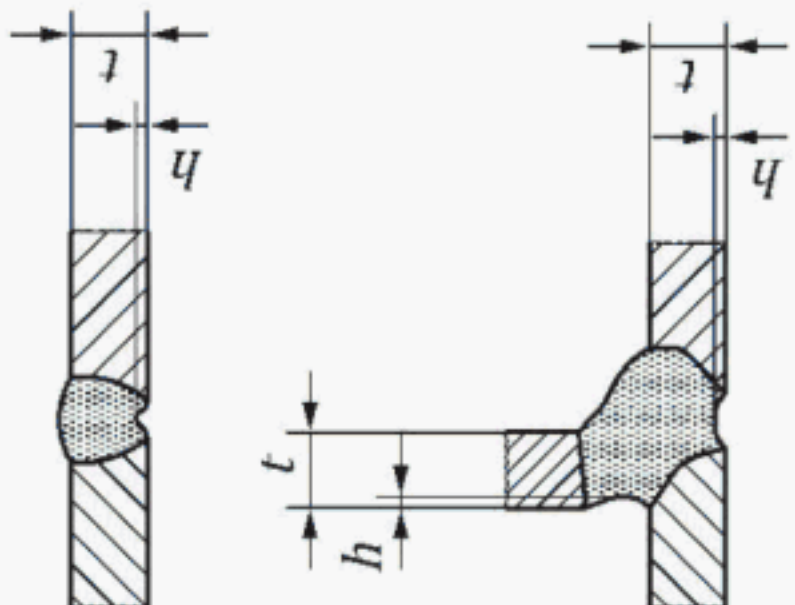
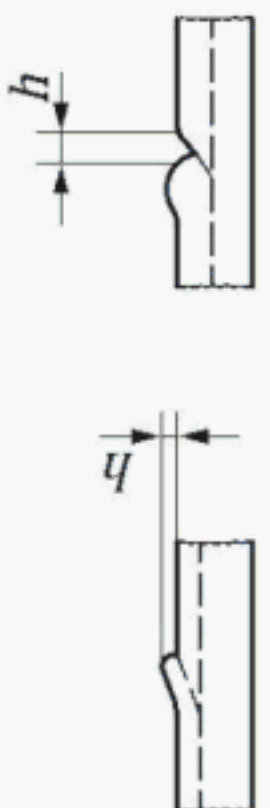
No.	Reference No. in ISO 6520-1	Designation of imperfection	Remarks	t mm	Limits on imperfections for quality levels		
					D	C	B
1.16	509 511	Sagging Incompletely filled groove	Smooth transition required. 	≥0,5	Short imperfections		
					$h \leq 0,2t$ max. 1,5 mm	$h \leq 0,1t$ max. 1 mm	$h \leq 0,05t$ max. 0,5 mm
1.17	512	Excessive asymmetry of fillet weld (excessive unequal leg length)	Only for cases where a symmetric fillet weld has been specified. 	≥0,5	$h \leq 3 \text{ mm} + 0,3a$	$h \leq 2 \text{ mm} + 0,25a$	$h \leq 1,5 \text{ mm} + 0,2a$
1.18	515	Root concavity	Smooth transition required. 	≥0,5	Short imperfections		
					$h \leq 0,2t$ max. 1,5 mm	$h \leq 0,1t$ max. 1 mm	$h \leq 0,05t$ max. 0,5 mm
1.19	517	Poor restart		≥0,5	Permitted The limit depends on the type of imperfection occurred due to restart.	Not permitted	Not permitted

Table 1 (continued)

No.	Reference No. in ISO 6520-1	Designation of imperfection	Remarks	t mm	Limits on imperfections for quality levels		
					D	C	B
1.20	601	Stray arc	—	≥0,5	Permitted for short imperfections	Not permitted	Not permitted
1.21	602	Spatter	—	≥0,5	Acceptance depends on application, e.g. material, corrosion protection	Acceptance depends on application, e.g. material, corrosion protection	Acceptance depends on application, e.g. material, corrosion protection
2 Internal imperfections							
2.1	100	Crack	All types of crack except microcracks and crater cracks.	≥0,5	Not permitted	Not permitted	Not permitted
2.2	1001	Microcrack	A crack usually only visible under the microscope (×50)	≥0,5	Permitted	Max. 0,6 mm × 0,02 mm but max. 4 imperfections per 2 mm × 2 mm	Max. 0,4 mm × 0,01 mm but max. 3 imperfections per 2 mm × 2 mm
2.3	2011	Gas pore	Maximum dimension of a single gas pore.	≥0,5	$d \leq 0,4s$ or $0,4a$ but max. 6 mm	$d \leq 0,3s$ or $0,3a$ but max. 5 mm	$d \leq 0,2s$ or $0,2a$ but max. 4 mm
2.4	2012	Uniformly distributed porosity	The assessment of porosity is done with respect to the cross-sectional area. See examples given in Annex A . The assessment of imperfections is done with respect to the projected area. See examples given in Annex A .	≥0,5	≤6 %	≤2 %	≤1 %
				0,5 to 3	≤6 %	≤2 %	≤1 %
				>3 to 12	≤10 %	≤4 %	≤2 %
				>12 to 30	≤15 %	≤6 %	≤3 %
				>30	≤20 %	≤8 %	≤4 %

Table 1 (continued)

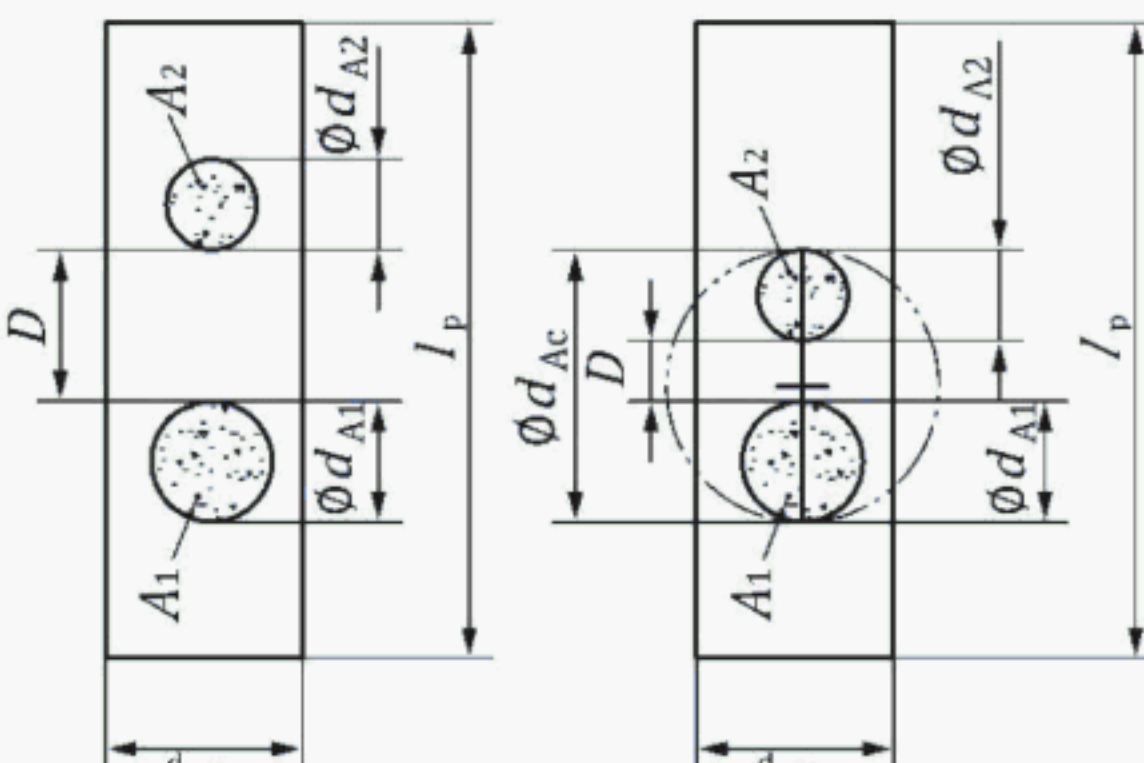
No.	Reference No. in ISO 6520-1	Designation of imperfection	Remarks	t mm	Limits on imperfections for quality levels		
2.5	2013	Clustered (local- ized) porosity		≥0,5	$d_A \leq 25 \text{ mm}$ or $d_{A,\text{max}} \leq w_p$	$d_A \leq 20 \text{ mm}$ or $d_{A,\text{max}} \leq w_p$	$d_A \leq 15 \text{ mm}$ or $d_{A,\text{max}} \leq w_p/2$

Table 1 (continued)

No.	Reference No. in ISO 6520-1	Designation of imperfection	Remarks	t mm	Limits on imperfections for quality levels		
					D	C	B
			Reference length for l_p is 100 mm. The total gas pore area within the cluster is represented by a circle of diameter d_A surrounding all the gas pores. The requirements for a single gas pore shall be met by all the gas pores within this circle. A permitted porous area shall be local. The possibility of the pore cluster masking other imperfections shall be taken into consideration. If D is less than d_{A1} or d_{A2} , whichever is smaller, then the total gas pore area is represented by a circle of diameter d_{Ac} , where $d_{Ac} = d_{A1} + d_{A2} + D$. Systematic clustered porosity is not permitted.		d_A corresponds to d_{A1} , d_{A2} or d_{Ac} whichever is applicable		
2.6	2014	Linear porosity	—	≥0,5	Short imperfections permitted	Not permitted	
2.7	2015 2016	Elongated cavity Wormhole	—	≥0,5	$l \leq 0,4s$ or $0,4a$ but max. 6 mm	$l \leq 0,3s$ or $0,3a$ but max. 4 mm	$l \leq 0,2s$ or $0,2a$ but max. 3 mm
2.8	303	Oxide inclusion	If several oxide inclusions $l_1, l_2, l_3, \dots, l_n$ exist in one cross-section, they are summed: $l = l_1 + l_2 + l_3 + \dots + l_n$.	≥0,5	Short imperfections		
					$l \leq s$ or a max. 10 mm	$l \leq 0,5s$ or $0,5a$ max. 5 mm	$l \leq 0,2s$ or $0,2a$ max. 3 mm
2.9	304	Metallic inclusion	—	≥0,5	$l \leq 0,4s$ or $0,4a$ but max. 6 mm	$l \leq 0,3s$ or $0,3a$ but max. 4 mm	$l \leq 0,2s$ or $0,2a$ but max. 3 mm

Table 1 (continued)

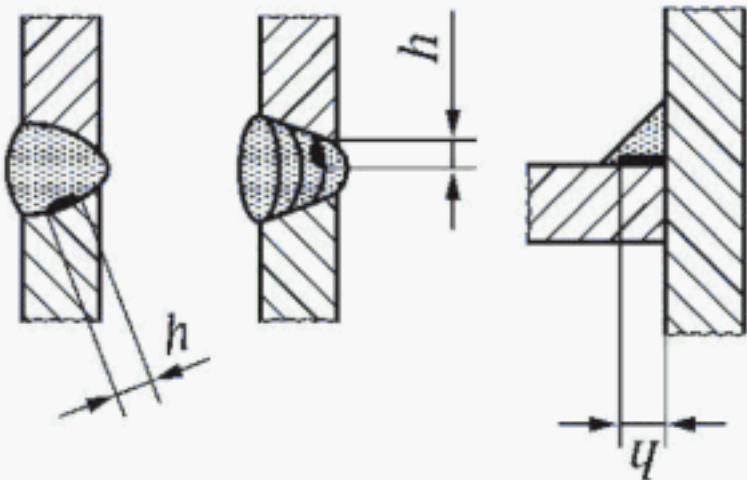
No.	Reference No. in ISO 6520-1	Designation of imperfection	Remarks	<i>t</i> mm	Limits on imperfections for quality levels		
					D	C	B
2.10	401	Lack of fusion (incomplete fusion)		≥0,5	Short imperfec- tions permitted $h \leq 0,4t$ or $0,4a$ but max. 3 mm	Short imperfec- tions permitted $h \leq 0,2t$ or $0,2a$ but max. 2 mm	Not permitted

Table 1 (continued)

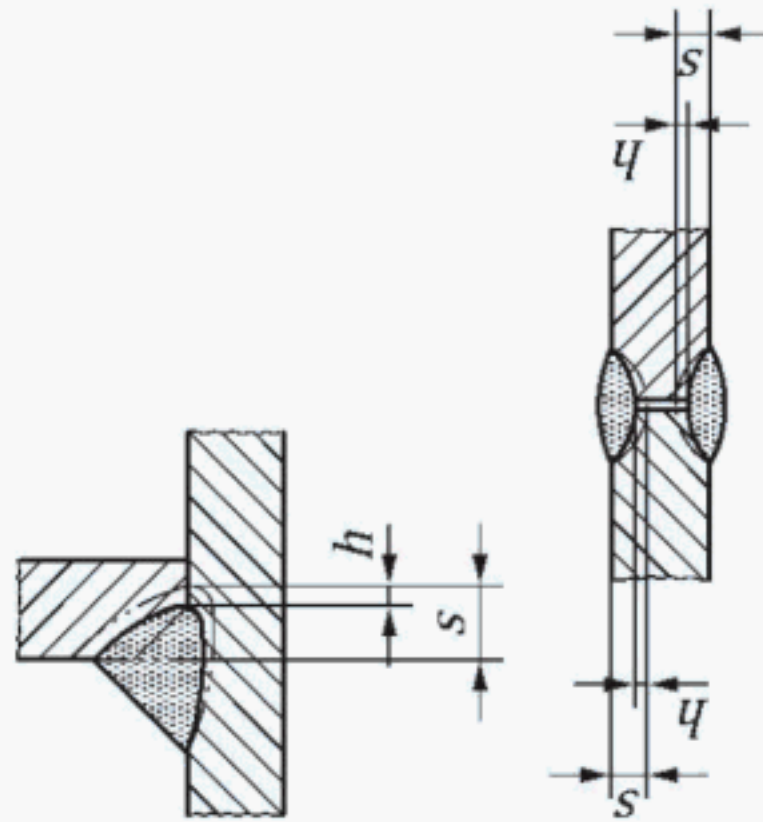
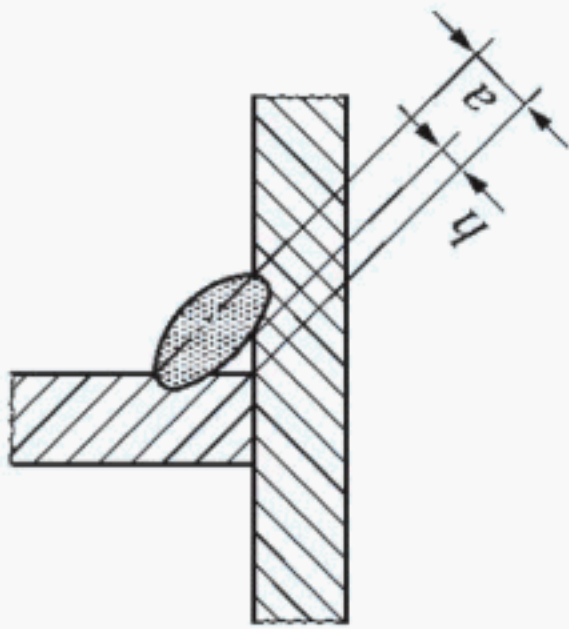
No.	Reference No. in ISO 6520-1	Designation of imperfection	Remarks	t mm	Limits on imperfections for quality levels			
					D	C	B	
2.11	402	Lack of penetration (incomplete penetration)	Partial penetration: 	≥0,5	Short imperfections, but not systematic imperfections	Not permitted		
					$h \leq 0,4s$ max. 4 mm		$h \leq 0,2s$ max. 2 mm	
				≥0,5	Short imperfection: $h \leq 0,2t$, but max. 2 mm		Not permitted	
2.12	4021	Incomplete root penetration for fillet welds		≥0,5	Short imperfections		Not permitted	
					$h \leq 0,4a$ max. 4 mm			$h \leq 0,2a$ max. 2 mm

Table 1 (continued)

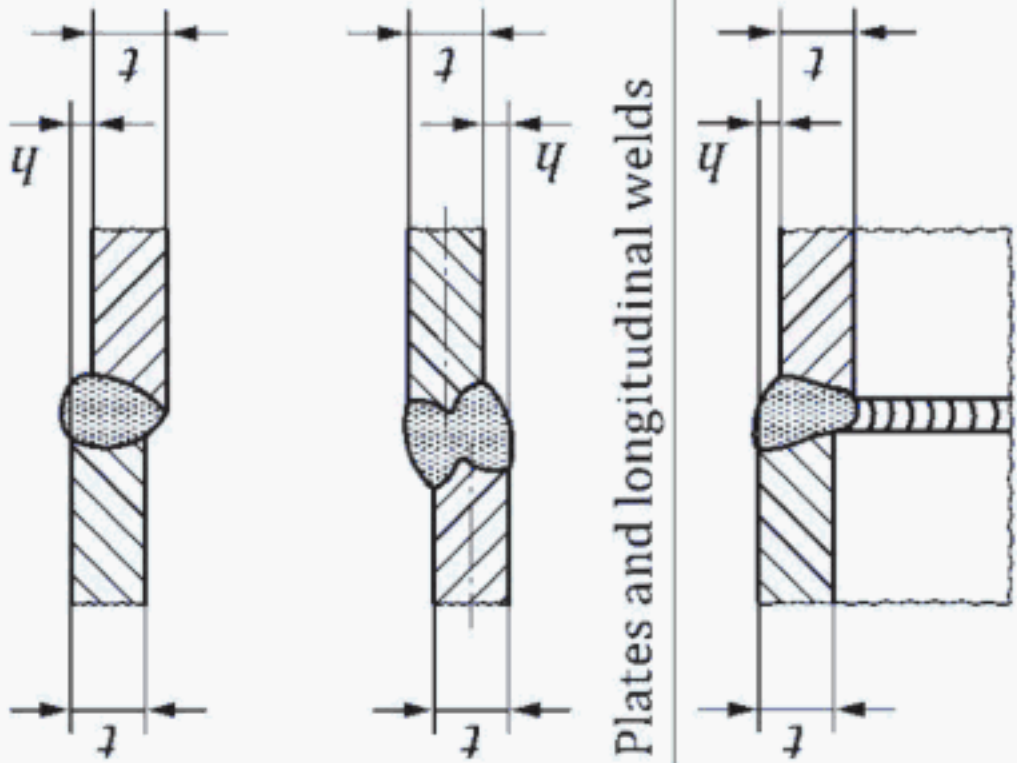
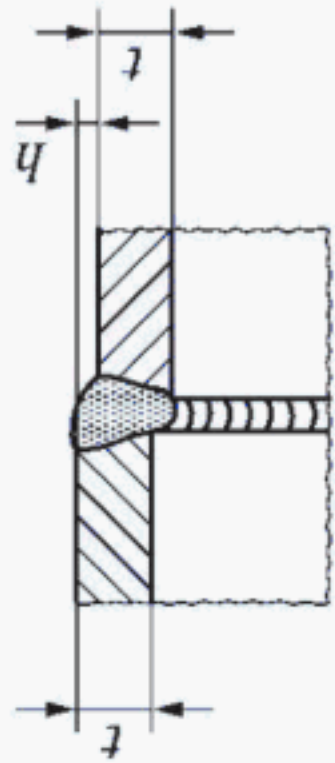
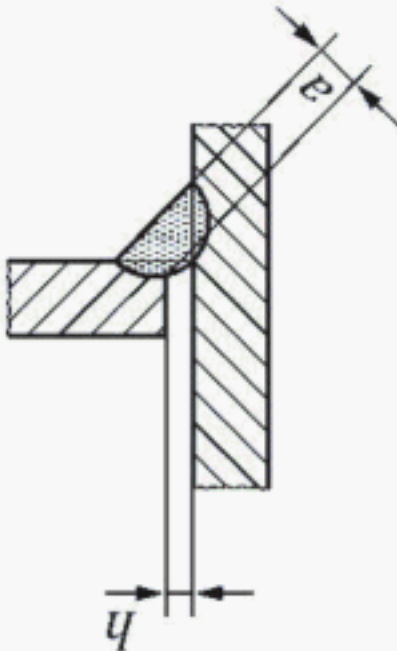
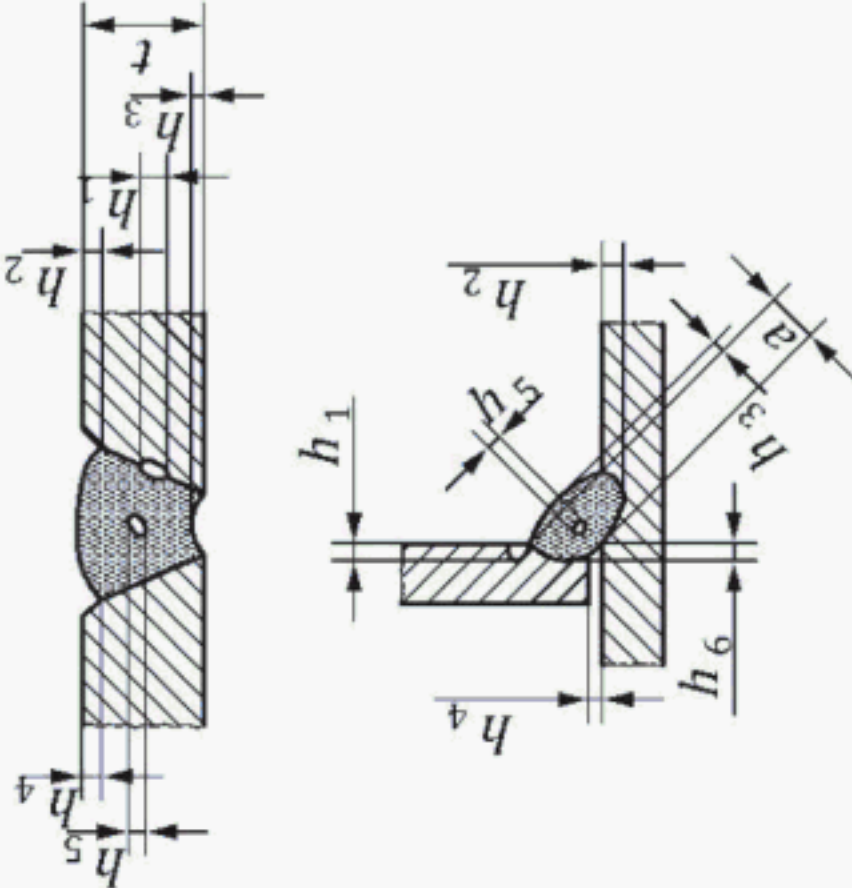
No.	Reference No. in ISO 6520-1	Designation of imperfection	Remarks	t mm	Limits on imperfections for quality levels		
					D	C	B
3 Imperfections in joint geometry							
3.1	507	Linear misalign- ment	<p>The limits relate to deviations from the correct position. Unless otherwise specified, the correct position is that when the centrelines coincide.</p> <p>t refers to the smaller thickness.</p> 	≥0,5	$h \leq 0,4t$ max. 8 mm	$h \leq 0,3t$ max. 4 mm	$h \leq 0,2t$ max. 2 mm
			<p>Plates and longitudinal welds</p> 	≥0,5	$h \leq 0,4t$ max. 10 mm	$h \leq 0,3t$ max. 6 mm	$h \leq 0,2t$ max. 4 mm

Table 1 (continued)

No.	Reference No. in ISO 6520-1	Designation of imperfection	Remarks	t mm	Limits on imperfections for quality levels		
3.2	617	Incorrect root gap for fillet welds	<p>Gap between the parts to be joined.</p>  <p>Gaps exceeding the relevant limit may in certain cases be compensated for by a corresponding increase in the throat thickness.</p>	≥0,5	$h \leq 1 \text{ mm} + 0,2a$ max. 5 mm	$h \leq 0,5 \text{ mm} + 0,15a$ max. 4 mm	$h \leq 0,5 \text{ mm} + 0,1a$ max. 3 mm
4 Multiple imperfections							
4.1	—	Multiple imperfections in any cross-section		≥0,5	The sum of the acceptable individual imperfections in any cross-section shall not exceed:		
					0,4t or 0,4a	0,3t or 0,3a	0,2t or 0,2a

Annex A (informative)

Examples of the determination of the percent porosity

Figures A.1 to A.10 illustrate different percent (%) porosities. They are intended to assist in the assessment of porosity in projected areas (radiographs) or in cross-sectional areas.



Figure A.1 — 0,5 %



Figure A.2 — 1 %



Figure A.3 — 2 %



Figure A.4 — 3 %



Figure A.5 — 4 %

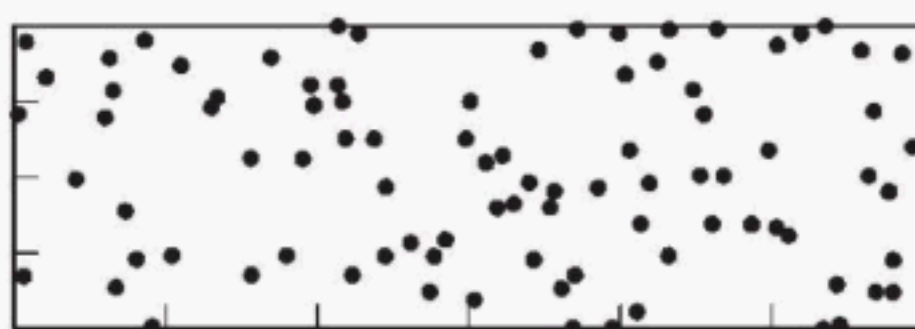


Figure A.6 — 6 %

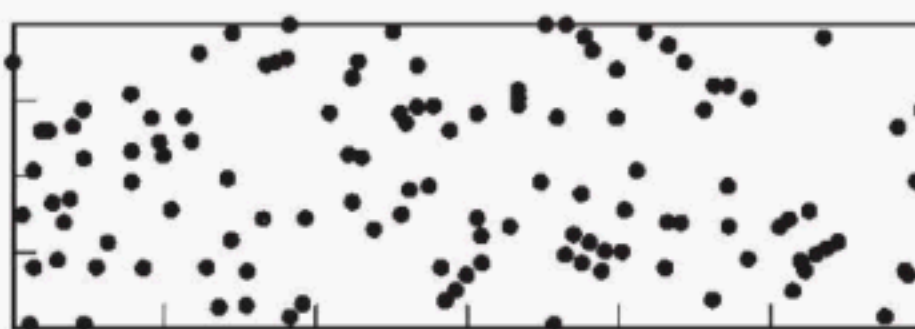


Figure A.7 — 8 %

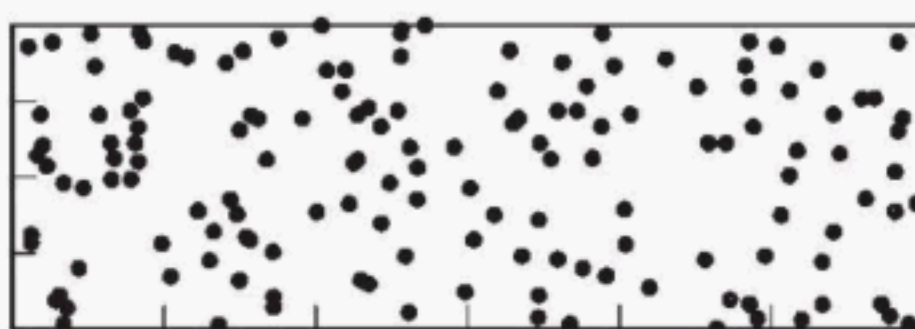


Figure A.8 — 10 %

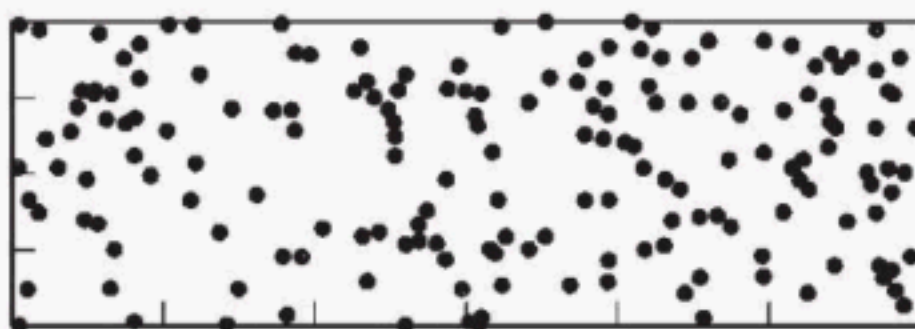


Figure A.9 — 15 %

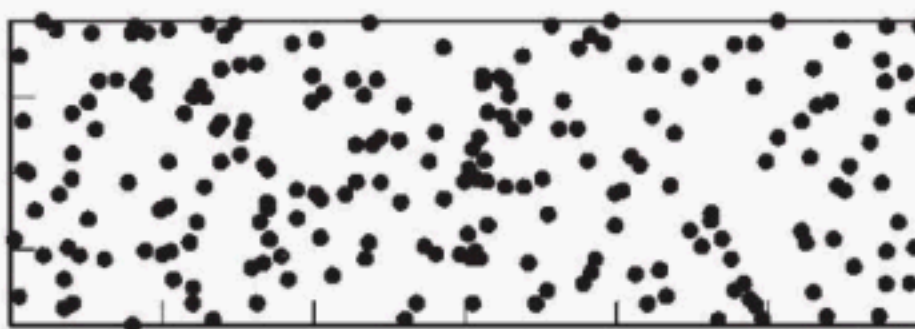


Figure A.10 — 20 %

Annex B (informative)

Additional information and guidelines for users of this document

This document specifies requirements for three quality levels for imperfections in welded joints of aluminium and its alloys produced by arc welding processes (beam welding excluded), as specified in the Scope, and for weld thicknesses $\geq 0,5$ mm. It may be used, where applicable, for other arc welding processes and weld thicknesses.

Components are very often produced for different applications, but to similar requirements. The same requirements should, however, apply to identical components produced in different workshops to ensure that work is carried out using the same criteria. The consistent application of this document is one of the fundamental cornerstones of a quality assurance system for use in the production of welded structures.

When summing multiple imperfections, there is a theoretical possibility of individual imperfections being superimposed. In such a case, the summation of all permitted deviations should be restricted by the values specified for the various imperfections, i.e. the limit for a single imperfection, e.g. a single pore, should not be exceeded.

This document may be used in conjunction with a catalogue of realistic illustrations showing the sizes of the permissible imperfections for the various quality levels by means of photographs showing the face and root side and/or reproductions of radiographs and of photomacrographs showing the cross-section of the weld. An example of such a catalogue is Reference [4] which can be used with reference cards to assess the various imperfections and employed when opinions differ as to the permissible size of imperfections.

Bibliography

- [1] [ISO 2553](#), *Welding and allied processes — Symbolic representation on drawings — Welded joints*
- [2] [ISO 13919-2](#), *Welding — Electron and laser beam welded joints — Guidance on quality levels for imperfections — Part 2: Aluminium and its weldable alloys*
- [3] [ISO 17635](#), *Non-destructive testing of welds — General rules for metallic materials*
- [4] Reference radiographs for the assessment of weld imperfections according to ISO 10042, published by the International Institute of Welding (IIW) and Deutscher Verlag für Schweißen und verwandte Verfahren, Düsseldorf

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.
- Standards purchased in hard copy format:
- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions. With British Standards Online (BSOL) you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a BSI Subscribing Member. PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a Multi-User Network Licence (MUNL) you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email:

knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

This page deliberately left blank