



BSI Standards Publication

**Petroleum products and lubricants —
Determination of water washout
characteristics of lubricating greases**

National foreword

This British Standard is the UK implementation of [ISO 11009:2021](#).

The UK participation in its preparation was entrusted to Technical Committee PTI/13, Petroleum Testing and Terminology.

A list of organizations represented on this committee can be obtained on request to its committee manager.

Contractual and legal considerations

This publication has been prepared in good faith, however no representation, warranty, assurance or undertaking (express or implied) is or will be made, and no responsibility or liability is or will be accepted by BSI in relation to the adequacy, accuracy, completeness or reasonableness of this publication. All and any such responsibility and liability is expressly disclaimed to the full extent permitted by the law.

This publication is provided as is, and is to be used at the recipient's own risk.

The recipient is advised to consider seeking professional guidance with respect to its use of this publication.

This publication is not intended to constitute a contract. Users are responsible for its correct application.

© The British Standards Institution 2021
Published by BSI Standards Limited 2021

ISBN 978 0 539 06683 8

ICS 75.100

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 August 2021.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

INTERNATIONAL STANDARD

ISO
11009

Second edition
2021-08-12

Petroleum products and lubricants — Determination of water washout characteristics of lubricating greases

*Produits pétroliers et lubrifiants — Détermination de la résistance au
délavage à l'eau des graisses lubrifiantes*



Reference number
ISO 11009:2021(E)

© ISO 2021



COPYRIGHT PROTECTED DOCUMENT

© ISO 2021, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO’s member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents		Page
Foreword		iv
Introduction		v
1	Scope	1
2	Normative references	1
3	Terms and definitions	1
4	Principle	1
5	Sampling	2
6	Apparatus	2
7	Materials	2
8	Preparation of the apparatus	2
9	Operating procedure	3
10	Calculations	3
11	Expression of results	4
12	Precision	4
	12.1 General	4
	12.2 Repeatability, <i>r</i>	5
	12.3 Reproducibility, <i>R</i>	5
13	Test report	5
Annex A (informative) Set-up of apparatus		6
Bibliography		8

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 28, *Petroleum and related products, fuels and lubricants from natural or synthetic sources*.

This second edition cancels and replaces the first edition (ISO 11009:2000), which has been technically revised.

The main changes compared to the previous edition are as follows:

- addition of a rating of the appearance of the grease and of the water after test;
- addition of a note concerning the application of the test results to determine the symbol 3 “water contamination and rust protection” of [ISO 12924](http://www.iso.org/iso/12924) grease specifications.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

[ISO 6743-9](#) [[1](#)] classifies greases according to their conditions of use. The complete designation of a grease comprises of the ISO sign, the letter L (lubricant, industrial oils and related products), the letter X for the grease family, four symbols related to the conditions of use, and the NLGI consistency number. The third symbol is related to the ability of the grease to ensure satisfactory lubrication in presence of water and provide an adequate corrosion protection level.

The symbol 3 is a combination of the rust protection level evaluated using [ISO 11007](#) [[2](#)] and the level of resistance to water contamination using this document.

Greases are specified in [ISO 12924](#) [[3](#)].

A rolling bearing grease may be not suitable to lubricate plain bearings or gears.

Petroleum products and lubricants — Determination of water washout characteristics of lubricating greases

WARNING — The use of this document can involve hazardous materials, operations and equipment. This document does not purport to address all of the safety problems associated with its use. It is the responsibility of users of this document to take appropriate measures to ensure the safety and health of personnel prior to the application of the document, and to determine the applicability of any other restrictions for this purpose.

1 Scope

This document specifies a method for evaluating the resistance of a lubricating grease to washout by water from a bearing, when tested at 38 °C or 79 °C under specified laboratory test conditions.

This test method estimates the resistance of greases to washout from ball bearings under specified conditions. No formal correlation with field service has been established so far.

This document is used for development and specification purposes.

NOTE For the purposes of this document, the term “% (m/m)” is used to represent the mass fraction.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

[ISO 15](#), *Rolling bearings — Radial bearings — Boundary dimensions, general plan*

[ISO 1998-1](#), *Petroleum industry — Terminology — Part 1: Raw materials and products*

[ISO 3696](#), *Water for analytical laboratory use — Specification and test methods*

[ISO 23572](#), *Petroleum products — Lubricating greases — Sampling of greases*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in [ISO 1998-1](#) apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Principle

A test portion of grease is packed in a ball bearing inserted in a housing with specified clearances. The bearing is rotated at $63 \text{ rad/s} \pm 3 \text{ rad/s}$ ($600 \text{ min}^{-1} \pm 30 \text{ min}^{-1}$). Water, controlled at a specified test temperature, impinges on the bearing housing from a nozzle with a diameter of 1 mm, at a rate of $5 \text{ ml/s} \pm 0,5 \text{ ml/s}$. The distance between the end of the nozzle and the shield of the housing is 57 mm. The water jet is set to strike the bearing $6 \text{ mm} \pm 2 \text{ mm}$ above the upper edge of the shield. The amount of grease washed out in $60 \text{ min} \pm 5 \text{ min}$ is a measure of the resistance of the grease to water washout.

In addition, the washer fixed at the end of the rotating shaft shall be very well centred to ensure the 0,8 mm circular clearance with the shield. For that purpose, use a fitting screw, with a non-threaded part crossing the washer, the diameter of the non-threaded part being equal to that of the hole in the middle of the washer. See [Figure A.2](#).

9 Operating procedure

9.1 Carry out the test in duplicate. Fill the tared bearing ([6.2](#)) with $4,00 \text{ g} \pm 0,05 \text{ g}$ of test grease, equally distributed over the bearing. Insert the bearing and tared shields into the housing, and assemble the unit in the test apparatus. Record the mass of the bearing, shields and grease, to the nearest 0,01 g.

9.2 Add a minimum of 750 ml of preheated water ([7.2](#)) to the reservoir, but keep the water level below the bearing housing by means of a piece of tubing attached to the capillary discharge tube (key 4 on [Figure A.1](#)) or with a deflecting metal shield, until equilibrium temperature is attained. When the test is to be carried out at the higher temperature of $79,0 \text{ }^{\circ}\text{C} \pm 1,7 \text{ }^{\circ}\text{C}$, bring the water to the specified temperature by a previously selected source of heat. If the rig has one motor driving both the pump and test bearing, remove the belt from the test-bearing spindle pulley during the water warm-up time.

9.3 When the water reaches the specified temperature, adjust the by-pass valve to give a water-flow rate of $5 \text{ ml/s} \pm 0,5 \text{ ml/s}$ through the piece of tubing fixed on the capillary discharge tube and into the graduated cylinder ([6.3](#)). Determine the flow rate from the volume of liquid flowing into the cylinder over a period of 10 s, as measured with the timer ([6.4](#)). Remove the piece of tubing from the capillary discharge tube, and adjust the water jet so that it impinges on the shield 6,4 mm above the annular opening.

9.4 Start the test and continue operation for $60 \text{ min} \pm 5 \text{ min}$ from the moment when the rotational speed of the bearing reaches $63 \text{ rad/s} \pm 3 \text{ rad/s}$.

9.5 Shut off the motor and the heating source, if used. Remove the test bearing and shields and place them on a tared watch glass ([6.5](#)). The shields shall be separated from the bearing and placed with their inner faces upward to expose the wet grease to the air.

9.6 Dry the bearing and shields for 15 h at $77 \text{ }^{\circ}\text{C} \pm 6 \text{ }^{\circ}\text{C}$ (see NOTE) in the oven ([6.7](#)), and then weigh to the nearest 0,01 g to determine the grease mass loss. The grease remaining on the shields, and any leakage occurring during the drying period, should not be considered as grease mass loss.

NOTE In some cases, a mass increase and not a mass loss, can be noted. The origin can be building up of stable grease – water emulsion, from which the water cannot be evaporated in the foreseen drying conditions.

The drying temperature should be increased to $93 \text{ }^{\circ}\text{C} \pm 3 \text{ }^{\circ}\text{C}$ for greases containing high-viscosity oils, to facilitate removal of water during the time period specified.

9.7 Important mass loss can be encountered with grease containing very fluid base oils, that can partially evaporate under the specified drying conditions. In that case, it is advisable to carry out a blank test. The blank test is performed packing the bearing with the prescribed grease quantity as indicated in [9.1](#); then the bearing is placed in the test apparatus and rotated during 5 min to distribute the grease evenly in the bearing, but without applying the water circulation. Then operate as indicated in [9.6](#).

10 Calculations

The mass loss of grease by water washout, w , expressed in % (m/m), is calculated using [Formulae \(1\)](#), [\(2\)](#) and [\(3\)](#):

$$\Delta m_e = m_2 - m_1 \quad (1)$$

$$\Delta m_a = m_3 - m_1 \tag{2}$$

$$w = \frac{100 \cdot (\Delta m_e - \Delta m_a)}{\Delta m_e} \tag{3}$$

where

- Δm_e is the mass of grease before test, expressed in g;
- Δm_a is the mass of grease after test, expressed in g;
- m_1 is the mass of the bearing and shields, expressed in g;
- m_2 is the mass of grease, bearings and shields before test, expressed in g;
- m_3 is the mass of grease, bearing and shields, after test, expressed in g.

Report the mass loss, w , in % (m/m) rounded to the nearest whole percent.

11 Expression of results

11.1 Report the average of duplicate tests as the percentage mass of grease washed out at the test temperature, and indicate the temperature at which the bearing assembly and grease were dried. Round the mass percentage to the nearest whole percent.

11.2 Carry out a visual examination, using the following observations as applicable:

11.2.1 Aspect of the grease after test:

- appearance unchanged;
- grease emulsified;
- grease hardened;
- grease softened;
- grease leaking out from the bearing.

11.2.2 Aspect of the water after test:

- water clear;
- water with a milky appearance;
- water with supernatant oil.

12 Precision

12.1 General

The precision of the method, as obtained by statistical examination of interlaboratory test results (see Reference [5]), is given in 12.2 and 12.3.

NOTE [ISO 12924](#) grease specifications uses this test for the symbol 3 “water contamination and rust protection”. For symbol 3 G, H and I, the requirement is water washout losses < 10 % (m/m), and for D, E, F the requirement is < 30 % (m/m). Taking into account the poor precision of the water washout test, losses below 10 % (m/m) are very difficult to guaranty. For example, at a 2 % level, R is 5,6 % at 38 °C and 7,26 % at 79 °C.

12.2 Repeatability, r

The difference between two independent results obtained using this method for test material considered to be the same in the same laboratory, by the same operator using the same equipment within short intervals of time, in the normal and correct operation of the method that is expected to be exceeded with a probability of 5 % due to random variation, can be calculated using the following formulae:

$$\text{at } 38\text{ }^{\circ}\text{C}: r = 0,8(X + 2)$$

$$\text{at } 79\text{ }^{\circ}\text{C}: r = 0,6(X + 4,6)$$

where X is the average of two results given as mass fraction.

12.3 Reproducibility, R

The difference between two independent results obtained using this method for test material considered to be the same in different laboratories, where different laboratory means a different operator, different equipment, different geographic location, and under different supervisory control, in the normal and correct operation of the test that is expected to be exceeded with a probability of 5 % due to random variation, can be calculated using the following formulae:

$$\text{at } 38\text{ }^{\circ}\text{C}: R = 1,4(X + 2)$$

$$\text{at } 79\text{ }^{\circ}\text{C}: R = 1,1(X + 4,6)$$

where X is the average of two results given as mass fraction.


13 Test report

The test report shall contain at least the following information:

- a) a reference to this document, i.e. [ISO 11009:2021](#);
- b) the type and complete identification of the product tested;
- c) the result of the test (see [Clause 11](#));
- d) the aspect of the grease after test (see [11.2.1](#));
- e) the aspect of the water after test (see [11.2.2](#));
- f) any deviation, by agreement or otherwise, from the standard procedures specified;
- g) the date of the test.

Annex A
(informative)

Set-up of apparatus

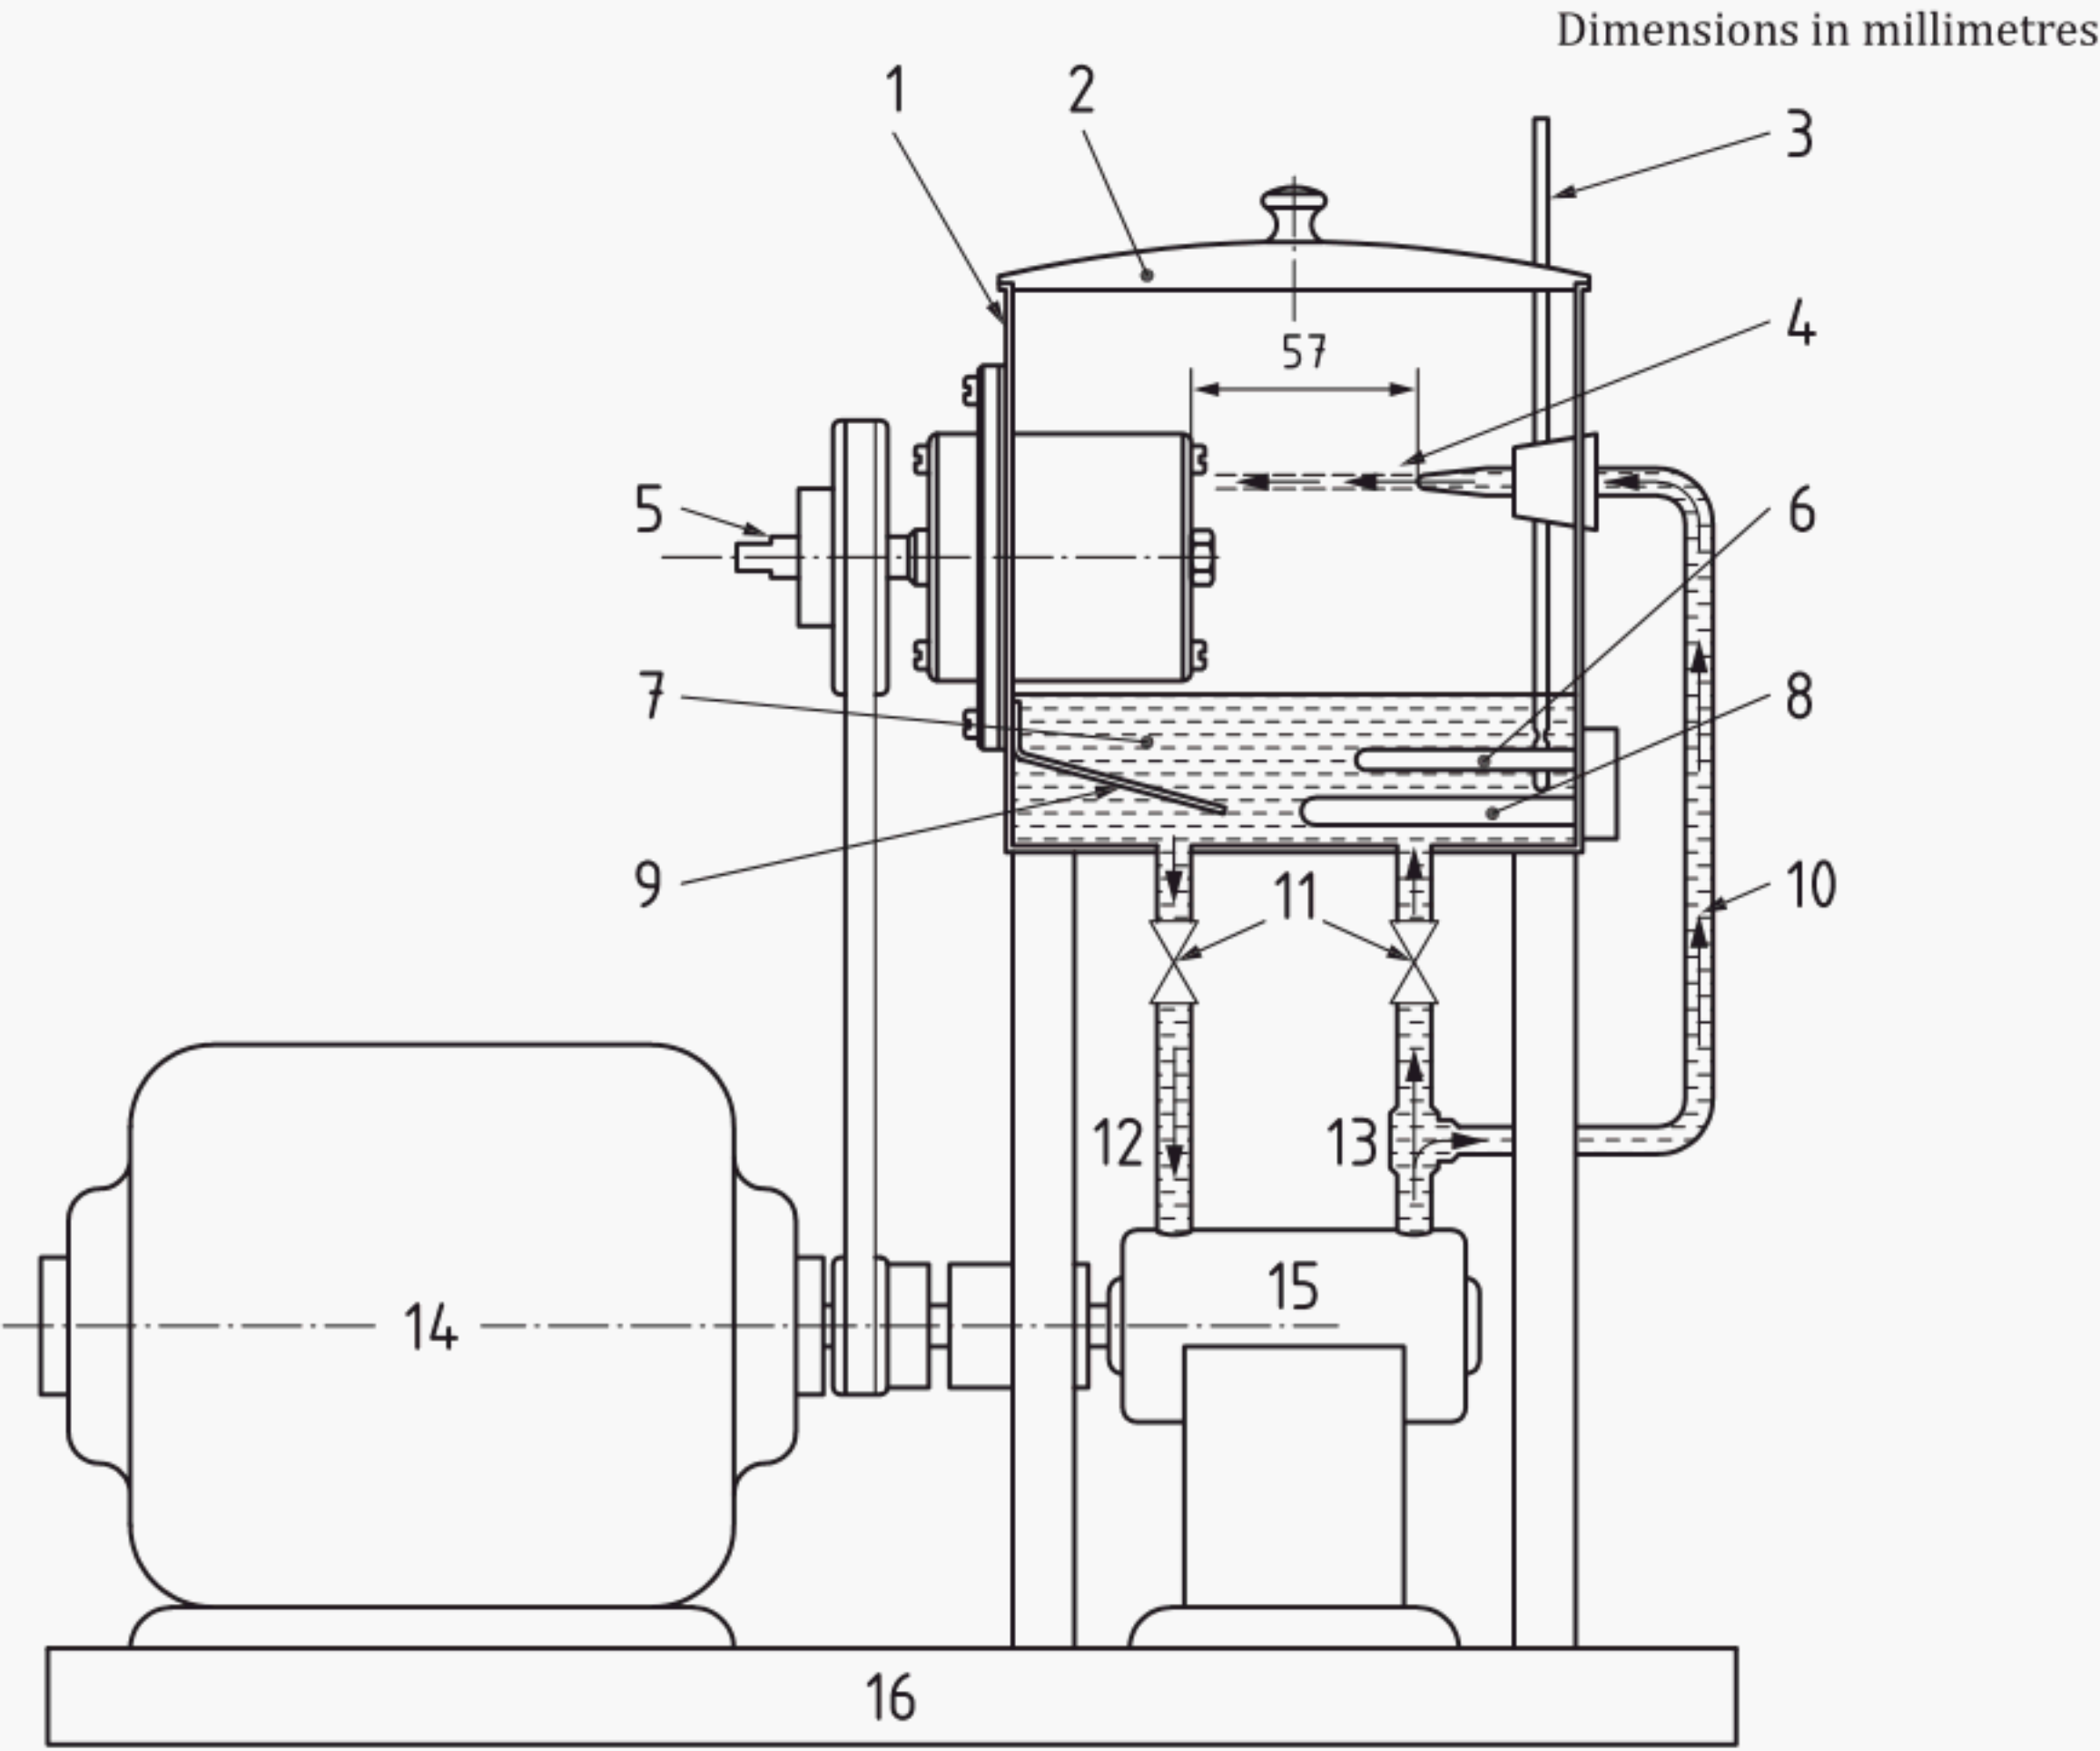


Key

- | | | | |
|---|--|----|--------------------------|
| 1 | tank (approximate size 150 mm × 150 mm × 150 mm) | 9 | baffle |
| 2 | cover | 10 | supply |
| 3 | thermometer | 11 | flow-rate control valves |
| 4 | water-jet flow rate: 5,0 ml/s ± 0,5 ml/s through 1 mm Ø capillary (discharge tube) | 12 | return |
| 5 | rotation speed of ball bearings: 63 rad/s ± 3 rad/s | 13 | bypass |
| 6 | thermostat | 14 | motor |
| 7 | 750 ml (min.) of distilled water in reservoir below the bearing housing | 15 | fluid pump |
| 8 | heater | 16 | base |

Figure A.1 — Suitable test rig apparatus

Dimensions in millimetres

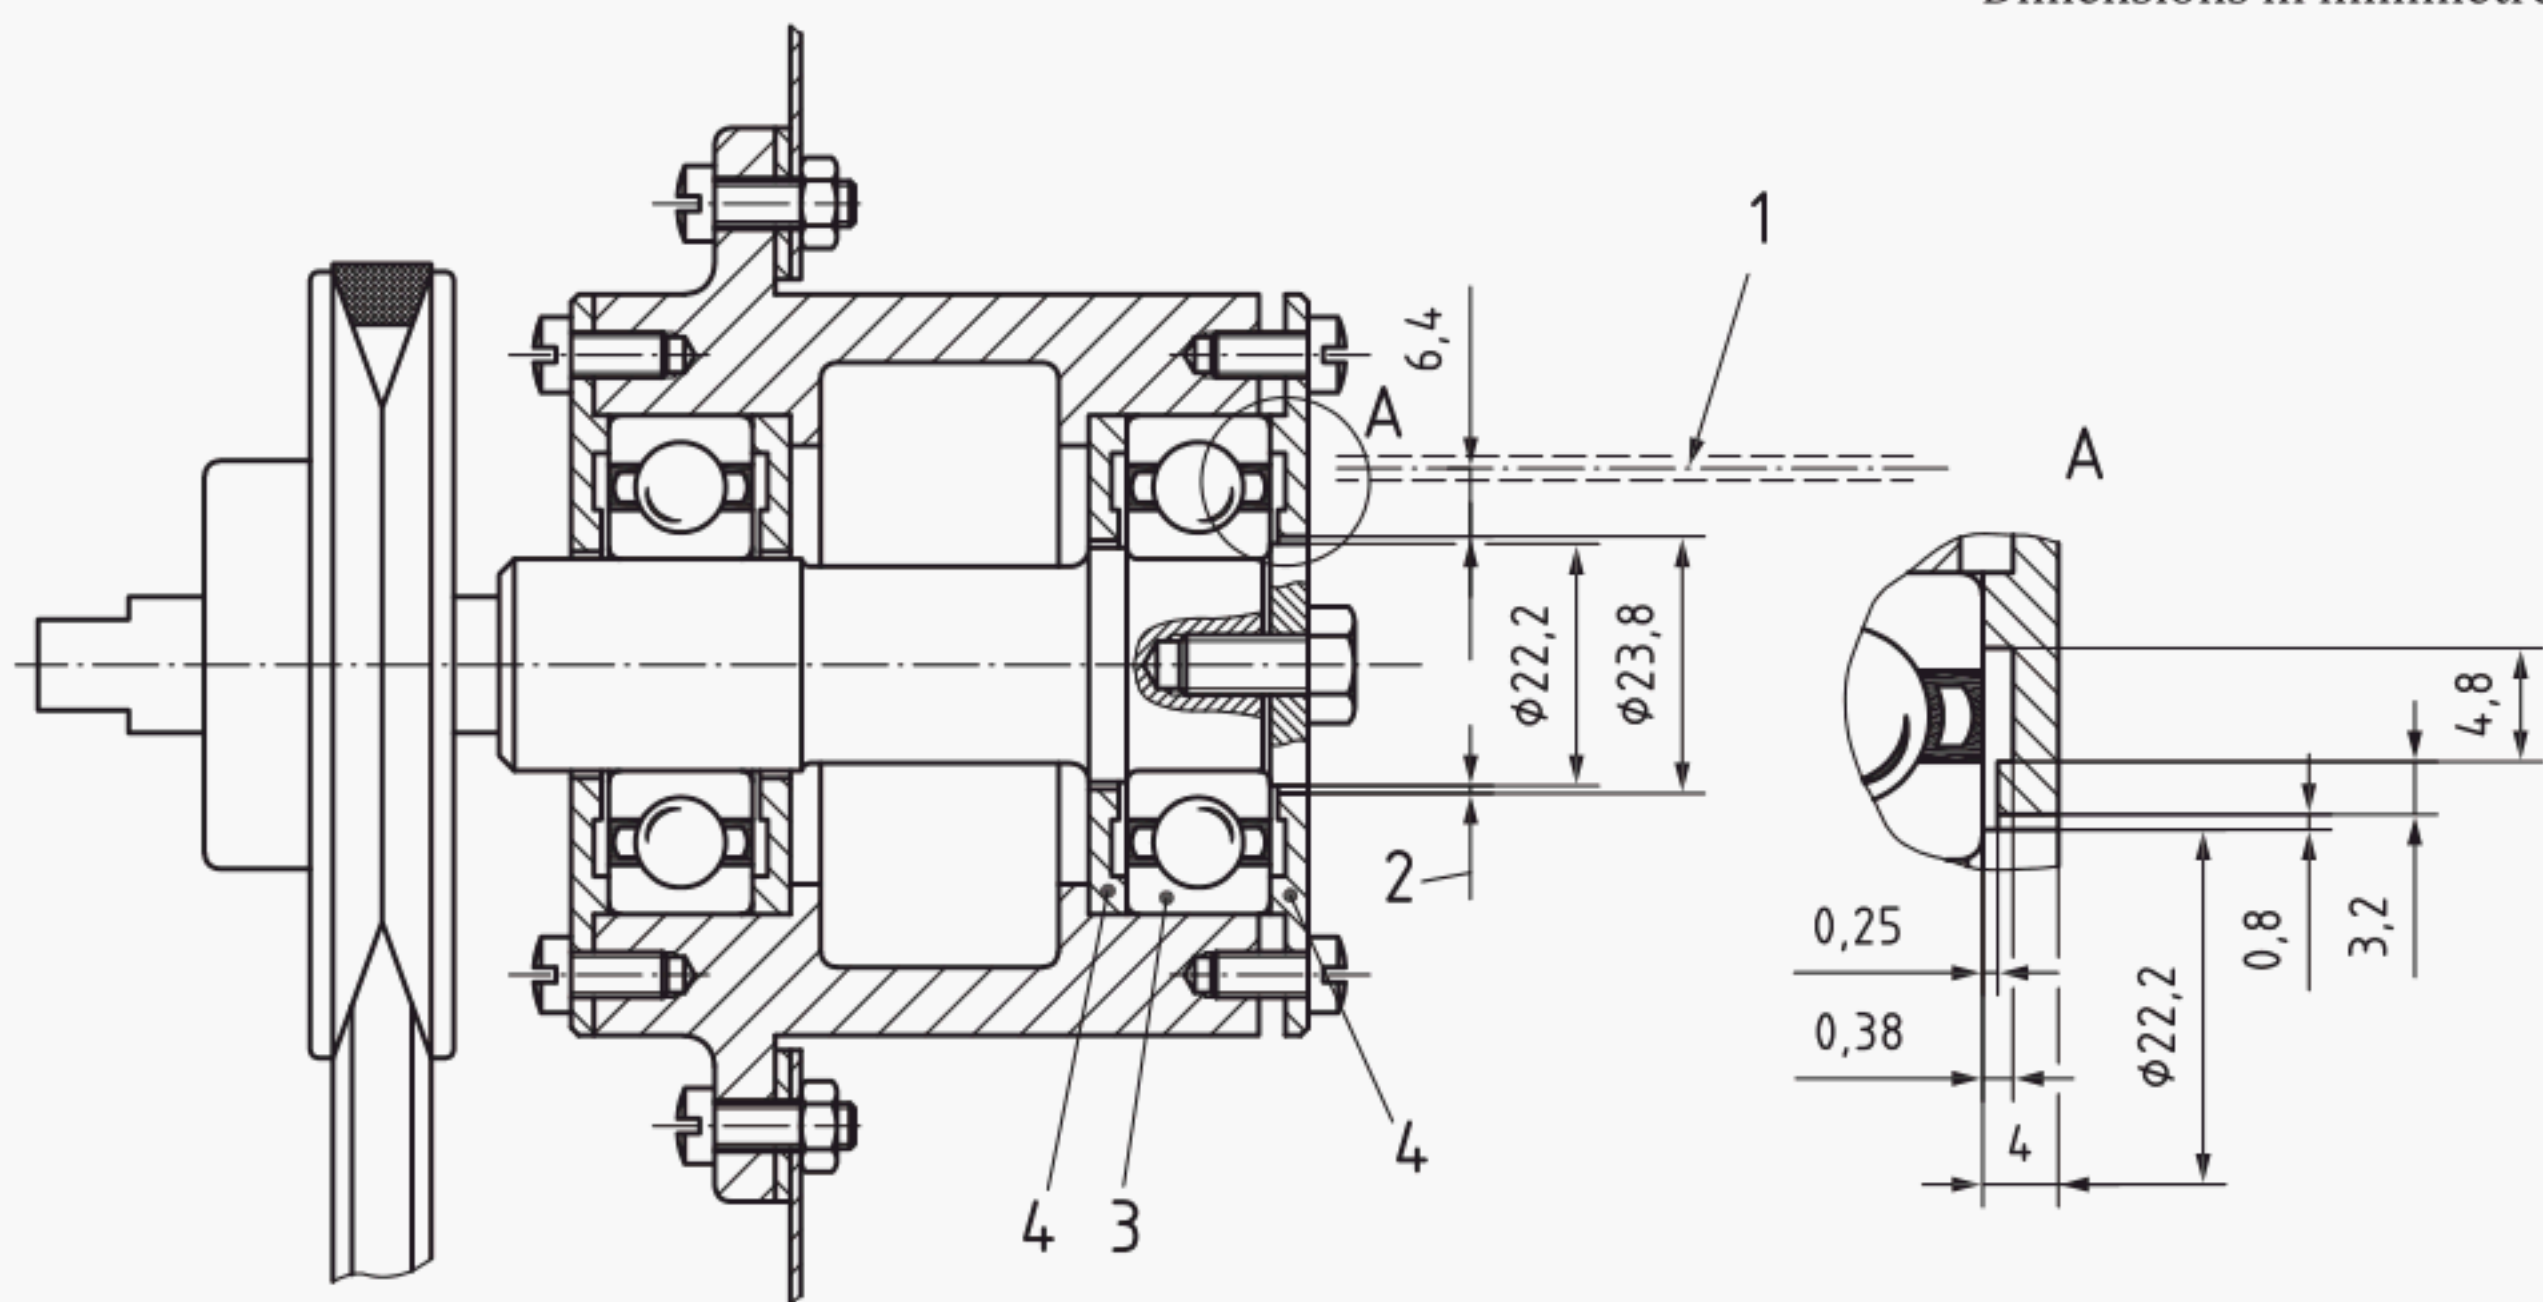

Key

- 1 centreline of capillary, \varnothing 1 mm
- 2 annular opening, 0,8 mm wide
- 3 test bearing of type 6204 - C3 clearance
- 4 shield

Figure A.2 — Typical cross-section of thrust-bearing assembly

Bibliography

- [1] [ISO 6743-9](#), *Lubricants, industrial oils and related products (class L) — Classification — Part 9: Family X (Greases)*
- [2] ISO 11007:1997¹⁾, *Petroleum products and lubricants — Determination of rust-prevention characteristics of lubricating greases*
- [3] [ISO 12924](#), *Lubricants, industrial oils and related products (Class L) — Family X (Greases) — Specification*
- [4] ASTM D235, *Standard Specification for Mineral Spirits (Petroleum Spirits) (Hydrocarbon Dry Cleaning Solvent)*
- [5] ASTM D1264, *Standard Test Method for Determining the Water Washout Characteristics of Lubricating Greases*
- [6] [BS 245](#), *Specification for mineral solvents (white spirit and related hydrocarbon solvents) for paints and other purposes*
- [7] NF T60-604, *Petroleum products — Lubricating greases — Resistance to water washout*

1) Now withdrawn and replaced by [ISO 11007-1](#) and [ISO/TS 11007-2](#).

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than one device provided that it is accessible by the sole named user only and that only one copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than one copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright and Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email cservices@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email: cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

