



BSI Standards Publication

Corrosion of metals and alloys — Sulfur dioxide test in a humid atmosphere (fixed gas method)

National foreword

This British Standard is the UK implementation of [ISO 22479:2019](#).

The UK participation in its preparation was entrusted to Technical Committee ISE/NFE/8, Corrosion of metals and alloys.

A list of organizations represented on this committee can be obtained on request to its secretary.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

© The British Standards Institution 2019
Published by BSI Standards Limited 2019

ISBN 978 0 580 98868 4

ICS 77.060

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 May 2019.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

INTERNATIONAL STANDARD

ISO
22479

First edition
2019-05-24

Corrosion of metals and alloys — Sulfur dioxide test in a humid atmosphere (fixed gas method)

*Corrosion des métaux et alliages — Essai au dioxyde de soufre en
atmosphère humide (méthode avec volume fixe de gaz)*



Reference number
ISO 22479:2019(E)

© ISO 2019



COPYRIGHT PROTECTED DOCUMENT

© ISO 2019, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO’s member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents		Page
Foreword		iv
Introduction		v
1	Scope	1
2	Normative references	1
3	Terms and definitions	1
4	Principle	1
5	Apparatus	1
5.1	Component protection.	1
5.2	Test cabinet.	2
5.3	Source of sulfur dioxide.	3
5.4	Conditioning of a new cabinet.	3
6	Test specimens	3
6.1	General	3
6.2	Dimensions	3
6.3	Preparation	3
6.3.1	Metals and alloys	3
6.3.2	Paints and varnishes	3
6.4	Arrangement of the test specimens	4
7	Test conditions	4
7.1	Test cycles	4
7.2	Test duration	5
8	Procedure	6
8.1	Introduction of water	6
8.2	Arrangement of the test specimens	6
8.3	Introduction of sulfur dioxide	6
8.4	Heating the test cabinet	6
8.5	Introduction of standard atmosphere	6
8.6	Replacement of water and sulfur dioxide	6
8.7	Cleaning of test specimens after test	6
8.7.1	General	6
8.7.2	Metals and alloys, metallic and non-organic coating test specimens	6
8.7.3	Organic coating test specimens	7
8.8	Performance check	7
9	Evaluation	7
10	Test report	7
Annex A (informative) Another example of a test cabinet		9
Annex B (informative) Performance check		10
Annex C (informative) Supplemental information		12
Bibliography		14

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT) see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 156, *Corrosion of metals and alloys*.

This first edition of ISO 22479 cancels and replaces [ISO 3231:1993](#) and [ISO 6988:1985](#), which have been combined and technically revised. The main changes compared with the previous edition are as follows:

- the method of generating sulfur dioxide from reagents has been deleted because of the risk of exposure to toxic chemicals.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Introduction

A humid atmosphere containing sulfur dioxide induces corrosion of many metals.

The results obtained in this document should not be regarded as a direct guide to the corrosion resistance of the tested materials in all environments where these materials may be used. Similarly, performances of different materials in this document should not be taken as a direct guide to the relative corrosion resistance of these materials in service.

It is appropriate to test only the same corrosion protection systems at the same time in one test procedure, because an interaction between samples can't be prevented. When testing different corrosion protection systems with different materials, it should be taken into account that the influence of sulfur dioxide often can be different.

The term “fixed gas method” means that at the beginning of the test a fixed volume of gas is introduced into a cabinet of fixed volume.

Corrosion of metals and alloys — Sulfur dioxide test in a humid atmosphere (fixed gas method)

WARNING — This document does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this document to establish appropriate safety and health practices.

1 Scope

This document specifies a method for assessing the resistance of materials or products to a humid atmosphere containing sulfur dioxide.

This method is applicable to testing metals and alloys, metallic and non-organic coatings and organic coatings.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

[ISO 1514](#), *Paints and varnishes — Standard panels for testing*

[ISO 2808](#), *Paints and varnishes — Determination of film thickness*

[ISO 8044](#), *Corrosion of metals and alloys — Basic terms and definitions*

3 Terms and definitions

For the purposes of this document, the terms and definitions given in [ISO 8044](#) apply.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:

- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Principle

The test specimens are exposed to a humid atmosphere containing sulfur dioxide. The sulfur dioxide dissolved by the moisture condenses on the test specimen surface and causes corrosion.

5 Apparatus

5.1 Component protection.

All components in contact with sulfur dioxide in a humid atmosphere shall be made of corrosion resistant materials, and shall themselves not emit any gas or vapour likely to influence corrosion of the test specimens.

5.3 Source of sulfur dioxide.

The source of sulfur dioxide should be a gas cylinder with a volume concentration of more than 99,9 %. It shall be fitted with appropriate regulating and measuring apparatus to ensure the supply of the correct volume of gas. The volume of gas delivered into the test cabinet should be measured by a calibrated flow meter. Another measuring instrument works with squeezing out a viscous liquid paraffin for the volume of the gas for 0,2, 1,0 and 2,0 l.

WARNING — Sulfur dioxide (CAS no. 7446-09-5) is toxic, corrosive and irritating. Handling of sulfur dioxide shall be restricted to skilled personnel or conducted under their control. The apparatus shall be used and maintained by skilled personnel, not only so that the procedures can be performed correctly, but also because of the hazards to health and safety that are involved.

5.4 Conditioning of a new cabinet.

In order to minimize the effect from the material of the cabinet by sulfur dioxide, a new cabinet shall be operated at least one test cycle in accordance with the procedures given in [8.2](#) to [8.5](#) without test specimens. The conditioning shall conform to [Table 1](#), with 2,0 l of sulfur dioxide.

6 Test specimens

6.1 General

The number, type, surface roughness, thickness of coatings, shape and dimensions of test specimens shall be selected according to the specification for the materials or product being tested. When not specified, details concerning the test specimens shall be agreed between the interested parties.

6.2 Dimensions

A typical specimen size is 150 mm × 100 mm by 0,75 mm to 1,25 mm thickness.

6.3 Preparation

6.3.1 Metals and alloys

Thoroughly clean the test specimens before testing. The cleaning method depends on the nature of the surface and the contaminants. Abrasives shall not include the use of any abrasives or solvents that may attack the surface of the test specimens. Take care that the test specimens are not recontaminated after cleaning, by excessive or careless handling.

If test specimens are cut from a large coated article, the cutting shall be carried out in such a way that the coating is not damaged, especially in the area adjacent to the cut. Unless otherwise specified, the cut edges should be adequately protected by coating with a suitable medium that is stable under the conditions of test, such as wax or adhesive tape.

6.3.2 Paints and varnishes

Unless otherwise specified or agreed, the test specimens shall be prepared in accordance with [ISO 1514](#) and then coated by the specified method with the product or system under test. The back and edges of the test specimens should be coated with the product or system under test.

Dry (or cure) and age (if applicable) each coated test specimen for the specified time and under the specified conditions and, unless otherwise specified, condition them at a temperature of $(23 \pm 2) ^\circ\text{C}$ and a relative humidity of $(50 \pm 5) \%$ for at least 16 h, with free circulation of air and not exposed to direct sunlight. The test procedure shall then be carried out as soon as possible.

Determine the thickness, in micrometres, of the dried coating by one of the non-destructive procedures described in [ISO 2808](#).

6.4 Arrangement of the test specimens

The distance between test specimens shall be not less than 20 mm. The distance between the edge of the test specimens and a wall of the test cabinet shall be not less than 100 mm. The test specimens shall be arranged in such a way that they cannot protect each other from the influence of the environment. The distance between the lowest edge of the test specimens and the surface of the water shall be greater than 200 mm. The contact area between test specimens and their supports shall be as small as possible.

The orientation of the exposed test surface in the test cabinet is critical. Unless otherwise specified, test specimen shall be mounted at an angle between vertical and $(15 \pm 2)^\circ$ to the vertical, with the area of primary interest facing up.

NOTE This is common practice for testing metallic specimens and measures to protect them from corrosion. When testing assemblies or enclosures, it is preferable to mount the specimen at the same angle as in typical use.

The total exposed surface area of the test specimens for one test shall be $(0,5 \pm 0,1) \text{ m}^2$ for each $(300 \pm 10) \text{ l}$ of the test cabinet. For different volumes of the test cabinet, the total exposed surface area is to be adjusted proportionally. When the total exposed surface area is less than $0,5 \text{ m}^2$ for 300 l of the cabinet, substitute specimens shall be added to obtain a total surface area of $0,5 \text{ m}^2$. The materials of the substitute specimens shall be the same as of the test specimens. Otherwise, test results may be different, since the influence (absorbance) of sulfur dioxide differs by materials.

7 Test conditions

7.1 Test cycles

One test cycle is 24 h, either Method A or Method B.

In Method A, test specimens are exposed to sulfur dioxide for 24 h. If test specimens are affected seriously by the temperature and humidity, Method B should be chosen.

In Method B, test specimens are exposed to sulfur dioxide for 8 h, followed by exposure to a standard atmosphere for 16 h.

The test conditions of Method A and Method B are shown in [Table 1](#) and [Table 2](#), respectively.

For metallic and non-organic coatings, 0,2 l volume of sulfur dioxide should be used. For paint and varnish, 0,2 l or 1,0 l volume of sulfur dioxide should be used. Generally, 0,2 l volume of sulfur dioxide is recommended where the coating thickness does not exceed approximately $40 \mu\text{m}$. 2,0 l volume of sulfur dioxide is used by agreement between the interested parties or according to product specifications, such as corrosion resistant coatings (e.g. hard chrome plating, anodised coating).

Table 1 — Test conditions of Method A

Conditions	Sulfur dioxide
One test cycle	24 h
Temperature	(40 ± 3) °C
Relative humidity	Approximately 100 %
Volume of sulfur dioxide	0,2 l, 1,0 l or 2,0 l [at (300 ± 10) l of capacity]
Quantity of water	(2,0 ± 0,2) l [at (300 ± 10) l of capacity]

NOTE 1 Theoretical concentrations of sulfur dioxide at the beginning of each test cycle are 0,067 %, 0,33 % and 0,67 %, corresponding to 0,2 l, 1,0 l and 2,0 l of sulfur dioxide gas, respectively. However, much of the sulfur dioxide is quickly dissolved into the water at the bottom of the test cabinet. Thus, the effective real sulfur dioxide concentration in the gas cabinet is much lower than the theoretical concentration (see Figure C.1).

NOTE 2 The ± tolerances given for the temperature are allowable fluctuations, which are defined as the positive and negative deviation from the setting of the sensor at the operational control set point during equilibrium conditions. This does not mean that the set value can vary by plus/minus the amount indicated from the given value.

Table 2 — Test conditions of Method B

Conditions	Sulfur dioxide	Standard atmosphere
Time of exposure	8 h	16 h
One test cycle	24 h	
Temperature	(40 ± 3) °C	(23 ± 5) °C
Relative humidity	Approximately 100 %	Less than 75 %
Volume of sulfur dioxide	0,2 l, 1,0 l or 2,0 l [at (300 ± 10) l of capacity]	—
Quantity of water	(2,0 ± 0,2) l [at (300 ± 10) l of capacity]	

NOTE 1 Theoretical concentrations of sulfur dioxide at the beginning of each test cycle are 0,067 %, 0,33 % and 0,67 %, corresponding to 0,2 l, 1,0 l and 2,0 l of sulfur dioxide gas, respectively. However, much of the sulfur dioxide is quickly dissolved into the water at the bottom of the test cabinet. Thus, the effective real sulfur dioxide concentration in the gas cabinet is much lower than the theoretical concentration (see Figure C.1).

NOTE 2 The ± tolerances given for the temperature are allowable fluctuations, which are defined as the positive and negative deviation from the setting of the sensor at the operational control set point during equilibrium conditions. This does not mean that the set value can vary by plus/minus the amount indicated from the given value.

7.2 Test duration

The test duration shall be as designated by the specification for the material or product being tested. When not specified, the test duration shall be agreed between the interested parties.

The test may be finished if a specified degree of corrosion has been reached, or if the appearance or function of test specimens has otherwise been impaired to an unacceptable level.

Recommended numbers of test cycles are: 1, 2, 5, 10, 15 or 20.

8 Procedure

8.1 Introduction of water

Introduce $(2,0 \pm 0,2)$ l of distilled or deionized water with a conductivity not higher than $5 \mu\text{S}/\text{cm}$ at $(25 \pm 2) ^\circ\text{C}$ inside the test cabinet.

NOTE This quantity is for 300 l capacity of the test cabinet. It depends on the capacity of the test cabinet proportionally (see [5.2](#)).

8.2 Arrangement of the test specimens

Place the test specimens in position (see [6.4](#)), and close tightly the test cabinet.

8.3 Introduction of sulfur dioxide

Introduce 0,2 l, 1,0 l or 2,0 l of sulfur dioxide at $(23 \pm 5) ^\circ\text{C}$ into the test cabinet through the gas inlet port.

NOTE This volume is for 300 l capacity of the test cabinet. It depends on the capacity of the test cabinet proportionally (see [5.2](#)).

The test cycle begins when sulfur dioxide is introduced.

8.4 Heating the test cabinet

The temperature of the test cabinet shall be raised to $(40 \pm 3) ^\circ\text{C}$ in less than 1,5 h and maintained for the specified period.

8.5 Introduction of standard atmosphere

In the case of Method B, the standard atmosphere is introduced by turning off the heater while opening and/or ventilating the test cabinet.

The temperature of the test cabinet shall be lowered to $(23 \pm 5) ^\circ\text{C}$, less than 75 % relative humidity in approximately 1 h and be maintained for the specified period.

Alternatively, the test specimens may be transferred to a different environmental cabinet capable of being maintained at the conditions of standard atmosphere.

8.6 Replacement of water and sulfur dioxide

The water and the sulfur dioxide in the test cabinet shall be replaced for each test cycle (24 h).

8.7 Cleaning of test specimens after test

8.7.1 General

Procedures for treatment of test specimens after testing shall be agreed between the interested parties before starting the test.

8.7.2 Metals and alloys, metallic and non-organic coating test specimens

At the end of the test cycle, remove the test specimens from the cabinet. Before they are examined, allow them to hang freely in a normal indoor atmosphere until any liquid corrosion products have solidified. First, examine them with all corrosion products in position. Any cleaning carried out shall depend on the criteria laid down for the evaluation of the results of the test.

8.7.3 Organic coating test specimens

At the end of the test cycle, remove the test specimens from the cabinet, blot them with absorbent paper and immediately examine the whole test surface of each test specimen for corrosion defects. Allow the test specimens to stand in the open at room temperature for 24 h. Then examine the test surface. If it is required to examine the substrate for signs of attack, remove the coating according to the specification for the materials or product being tested.

8.8 Performance check

In order to ensure the reproducibility and repeatability of test results obtained either with one or multiple test cabinets, performance checks shall be carried out. A suitable method for evaluation of the performance of the test cabinet by use of reference specimens is described in [Annex B](#).

9 Evaluation

Several different criteria for evaluation of the test results may be used to meet particular requirements, for example:

- a) appearance after test as described in the ISO 4628 series and [ISO 10289](#);
- b) appearance after removing superficial corrosion products described in the ISO 4628 series and [ISO 10289](#);
- c) number and distribution of corrosion defects, i.e. pits, cracks, blisters:
 - 1) in the case of metals and alloys, metallic and non-organic coatings be assessed by methods described in [ISO 10289](#);
 - 2) in the case of organic coatings, those be assessed by methods described in the ISO 4628 series;
- d) the time elapsed before the appearance of the first sign of corrosion;
- e) change in mass;
- f) alteration revealed by micrographic examination;
- g) change in mechanical properties.

10 Test report


The test report shall contain at least the following information:

- a) a reference to this document, i.e. ISO 22479:2019;
- b) the concentration of sulfur dioxide used;
- c) whether the test was performed in accordance with Method A or Method B (see [7.1](#));
- d) the specification of the base material;
- e) the type, dimensions, description and (if necessary) surface roughness of the test specimens;
- f) the preparation of the test specimens including any cleaning treatment applied and any protection given to edges or other special areas;
- g) the type of coating with an indication of its surface finish;
- h) the item of information related to the test specimen of paint and varnishes:
 - 1) duration and conditions of drying (or curing) and ageing (if applicable) the coating before test;

- 2) thickness of the dry coating and method of measurement;
- i) the number of test specimens of each coating or product subjected to the test;
- j) the methods, if any, used to clean the test specimens after test, with, when appropriate, an indication of the loss of mass resulting from the cleaning operation;
- k) the corrosivity of test determined as, for example, described in [Annex B](#);
- l) the temperature reading within the exposure zone of the test cabinet;
- m) the test duration;
- n) the angle of inclination of the test specimens during exposure;
- o) the character of any test specimens placed in the cabinet expressly to check the correctness of the operating conditions and the results obtained;
- p) the results of all inspections;
- q) any deviations from the procedure;
- r) any unusual features observed;
- s) the date of the test.

Annex A
(informative)

Another example of a test cabinet

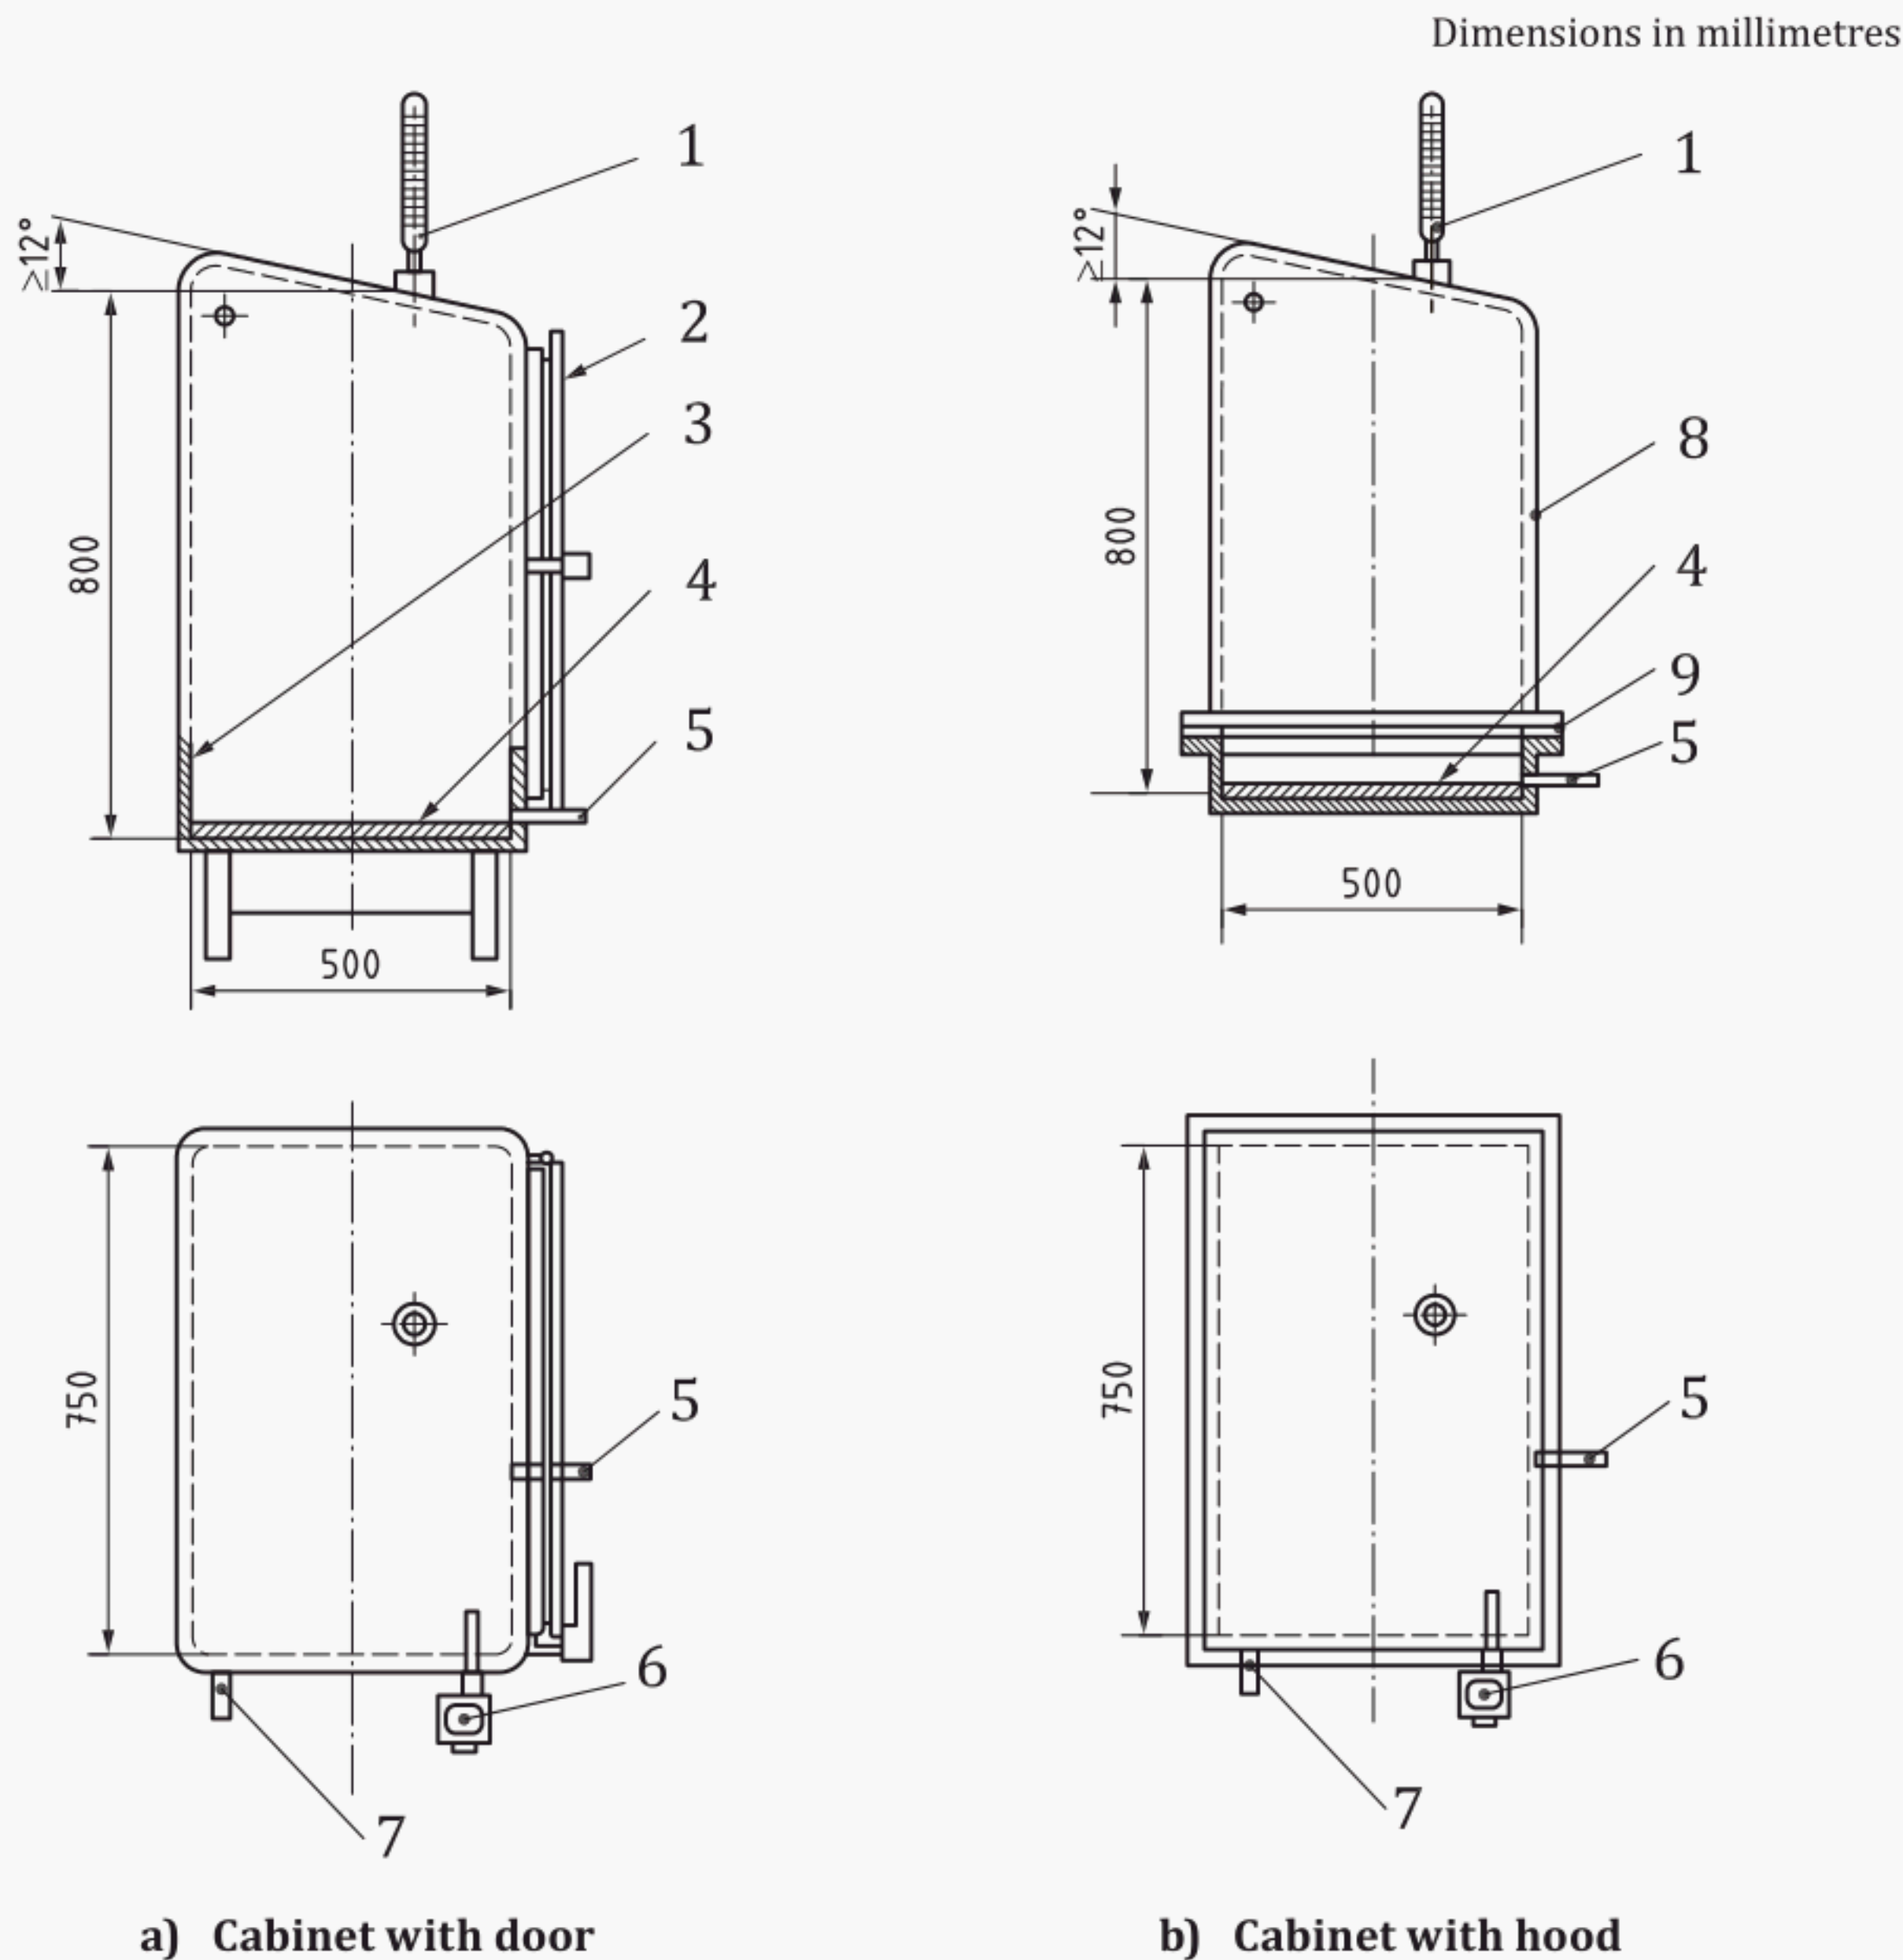

Key

- | | | | |
|---|---------------|---|-------------------------------|
| 1 | thermometer | 6 | temperature regulating device |
| 2 | door | 7 | pressure relief valve |
| 3 | water trough | 8 | hood |
| 4 | water surface | 9 | sealing strip |
| 5 | gas inlet | | |

Figure A.1 — Another example of a test cabinet

Annex B **(informative)**

Performance check

B.1 General

In order to ensure the reproducibility and repeatability of test results obtained either with one or several test apparatuses, performance checks may be performed.

This annex defines a test cabinet with 300 l capacity with 0,2 l volume of sulfur dioxide.

B.2 Reference specimens

The performance check is carried out using five reference specimens made of CR4-grade steel in accordance with ISO 3574. The dimensions of the reference specimens are 50 mm × 100 mm by 0,6 mm to 1,5 mm thickness.

In order to meet the requirement of total exposed surface area, $(0,5 \pm 0,1) \text{ m}^2$ (see [6.4](#)), two substitute specimens made of CR4-grade steel in accordance with ISO 3574 are required. The dimensions are 250 mm × 400 mm × 1 mm.

B.3 Preparation of reference specimens

Immediately prior to the test, clean the reference and substitute specimens carefully by eliminating all those traces (dirt, oil or other foreign matter) influencing the test results. Degrease with white spirit or some other suitable solvent using a soft, lint-free cloth or brush. Weigh the five reference specimens to an accuracy of 1 mg. If weighing cannot be made immediately after degreasing, they should be kept in a desiccator until weighing can be performed.

B.4 Procedure

B.4.1 Arrangement of reference specimens

The five reference specimens are placed vertically in the test cabinet and the two substitute specimens positioned vertically on either side of them in accordance with [6.4](#).

B.4.2 Test conditions

The five test cycles shall be performed in accordance with test conditions of Method B in [Table 2](#), with 0,2 l of sulfur dioxide.

B.4.3 Removal of corrosion products

At the end of the test, immediately take the reference specimens out of the test cabinet. The corrosion products can be removed from the reference specimens by pickling carried out at a temperature of 18 °C to 28 °C. Then, hydrochloric acid with a density $\rho = 1,10 \text{ g/ml}$ and inhibited with 3,5 g hexamethylenetetramine per litre (e.g. by making up 500 ml of chemically pure HCl, $\rho = 1,19 \text{ g/ml}$, to 1 l with distilled or deionized water) or 200 g of diammonium hydrogen citrate $[(\text{NH}_4)_2\text{HC}_6\text{H}_5\text{O}_7]$ (recognized analytical grade) per litre in distilled or deionized water for 10 min at 23 °C can be used.

Other solutions as specified in [ISO 8407](#) may be used.

B.4.4 Weighing of reference specimens

After removal of the corrosion products, the reference specimens are rinsed thoroughly in distilled or deionized water and dried. They are weighed to an accuracy of 1 mg. If they cannot be weighed immediately after drying, they are to be kept in a desiccator until weighing can be performed.

B.5 Expression of results

The loss in mass determined shall be expressed as a function of the total area exposed to corrosion, in g/m². For a successful performance check, the mean value shall be (145 ± 35) g/m², with individual values not deviating from the mean value by more than 20 %.


Annex C
(informative)

Supplemental information

C.1 Feature of fixed gas method

This test method is the introduction of a fixed volume of sulfur dioxide into the enclosed space with saturated humid atmosphere. The sulfur dioxide is dissolved into the moisture and its concentration is rapidly decreased. The degree of condensation on the test specimen surface depends on temperature/humidity around the test cabinet, the surface area and surface roughness of test specimens.

Figure C.1 shows an example of change in concentration of sulfur dioxide in the test cabinet without test specimens.

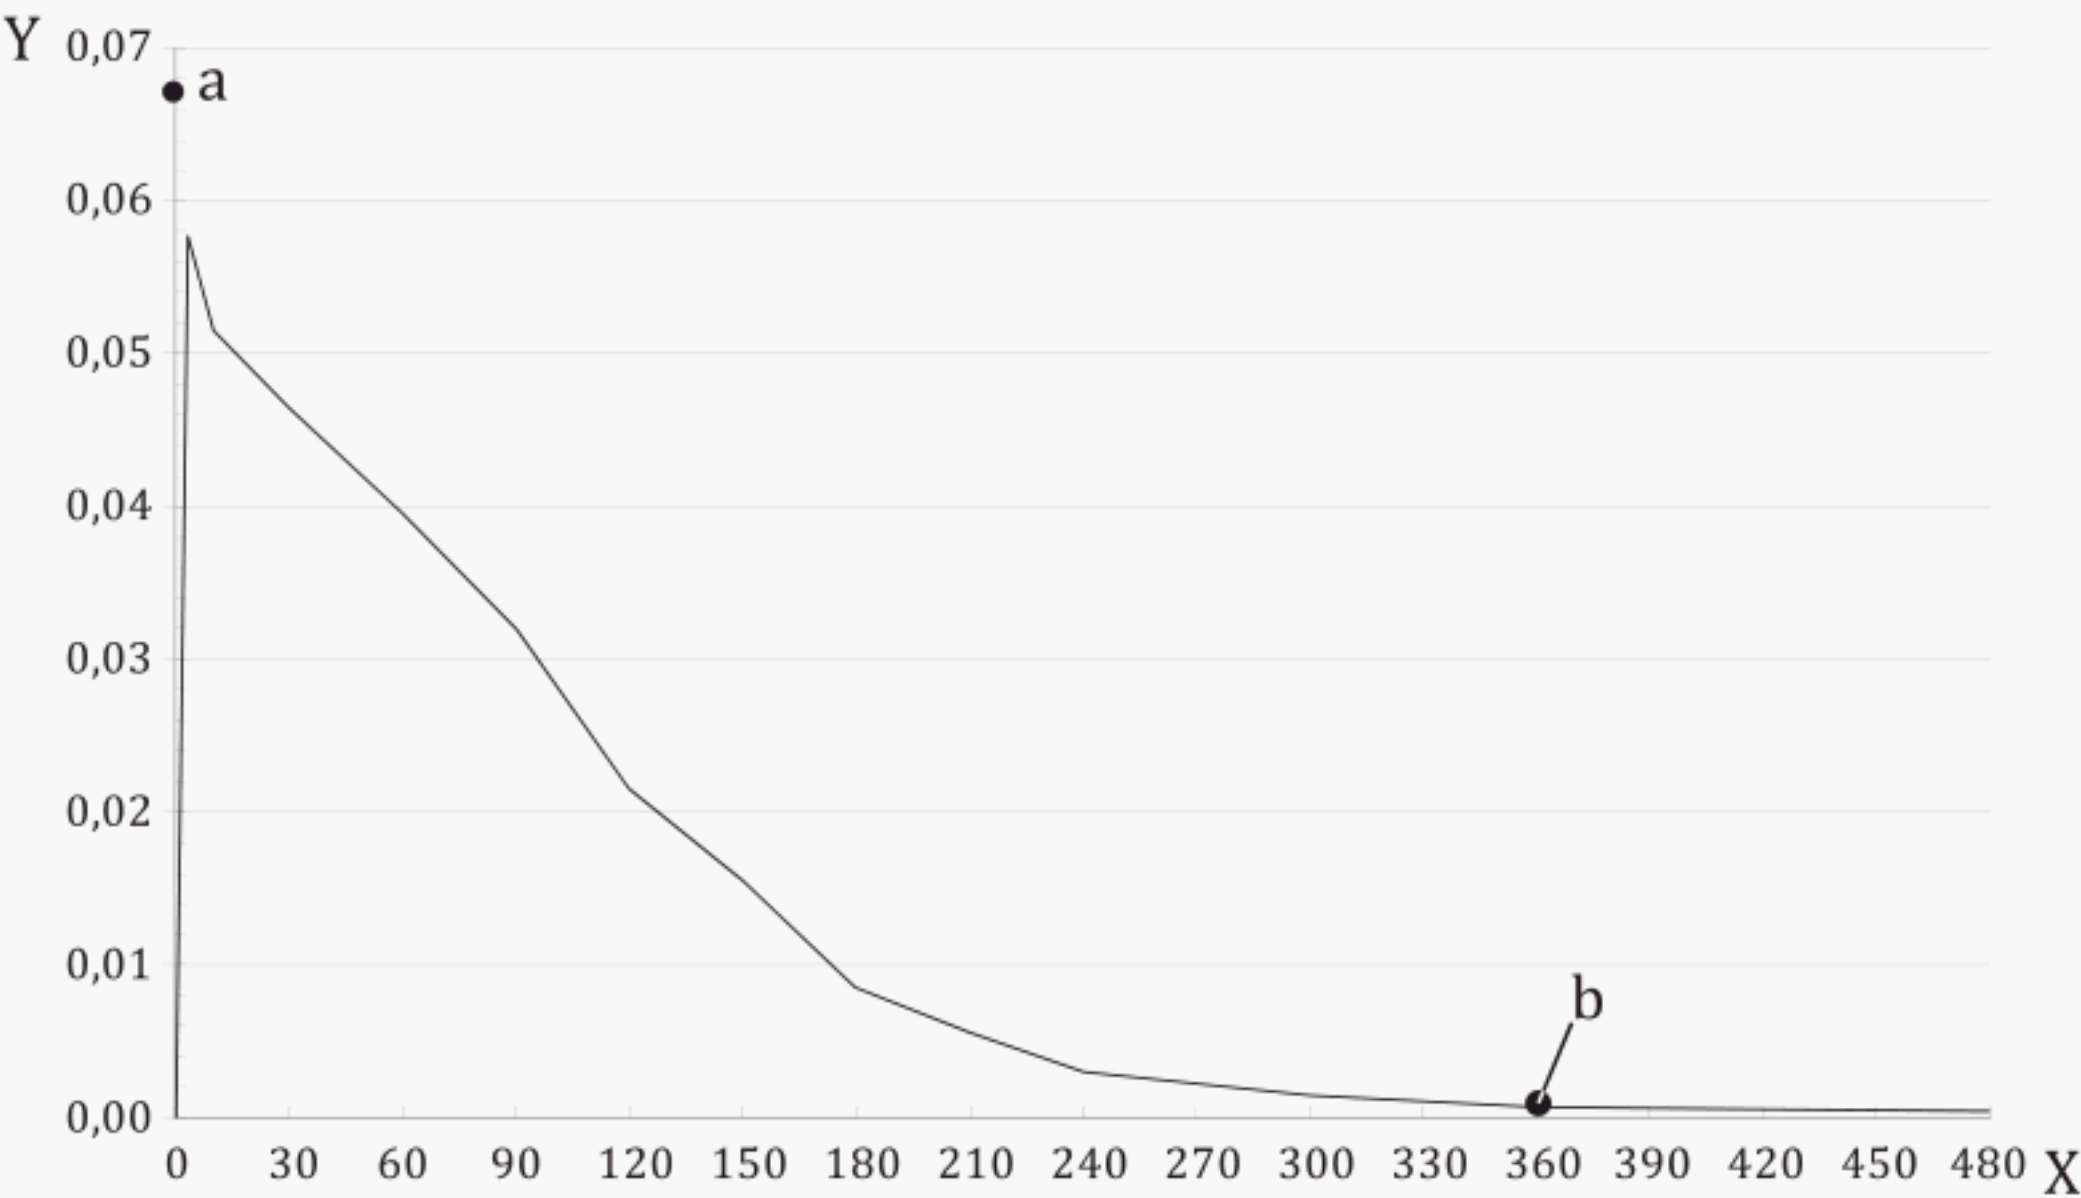

Key

- X test duration, expressed in minutes
- Y concentration of sulfur dioxide, expressed in percentage (%)
- a Introduction of 0,067 % concentration of sulfur dioxide.
- b Concentration of sulfur dioxide is 0,001 % or less at 360 min.

Test conditions are as follows:

- temperature: 40 °C
- relative humidity: approximately 100 %
- test duration: 8 h (480 min)

NOTE These data are submitted by Suga Test Instruments Co., Ltd.

Figure C.1 — An example of change in concentration of sulfur dioxide in the test cabinet

C.2 Information for paints and varnishes

C.2.1 A volume of 0,2 l sulfur dioxide in the 300 l test cabinet is generally recommended for testing coatings of thickness not exceeding approximately 40 µm.

C.2.2 Different types of films absorb sulfur dioxide at different rates and to different extents. Therefore, test results may be affected by the types of test specimen included in the test cabinet during testing. For example, the inclusion of oil paints and matt paints containing reactive basic pigments will reduce the severity of the test for other test specimens.

C.3 Flowing gas method

An alternative test method is based on flowing air with a specified constant concentration of sulfur dioxide and controlling the concentration at the test specimens. This test method is specified in [ISO 10062](#).

Bibliography

- [1] ISO 3574, *Cold-reduced carbon steel sheet of commercial and drawing qualities*
- [2] ISO 4628 (all parts), *Paints and varnishes — Evaluation of degradation of coatings — Designation of quantity and size of defects, and of intensity of uniform changes in appearance*
- [3] [ISO 8407](#), *Corrosion of metals and alloys — Removal of corrosion products from corrosion test specimens*
- [4] [ISO 10062](#), *Corrosion tests in artificial atmosphere at very low concentrations of polluting gas(es)*
- [5] [ISO 10289](#), *Methods for corrosion testing of metallic and other inorganic coatings on metallic substrates — Rating of test specimens and manufactured articles subjected to corrosion tests*
- [6] [ISO 17872](#), *Paints and varnishes — Guidelines for the introduction of scribe marks through coatings on metallic panels for corrosion testing*
- [7] DIN 50018, *Testing in a saturated atmosphere in the presence of sulfur dioxide*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit, or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than 1 device provided that it is accessible by the sole named user only and that only 1 copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.
- Standards purchased in hard copy format:
- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than 1 copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright & Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email subscriptions@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK