

BSI Standards Publication

**Rubber, vulcanized or thermoplastic —
Determination of tendency to adhere
to and corrode metals**

National foreword

This British Standard is the UK implementation of [ISO 6505:2021](#). It supersedes [BS ISO 6505:2015](#), which is withdrawn.

The UK participation in its preparation was entrusted to Technical Committee PRI/22, Testing and analysis of rubber.

A list of organizations represented on this committee can be obtained on request to its committee manager.

Contractual and legal considerations

This publication has been prepared in good faith, however no representation, warranty, assurance or undertaking (express or implied) is or will be made, and no responsibility or liability is or will be accepted by BSI in relation to the adequacy, accuracy, completeness or reasonableness of this publication. All and any such responsibility and liability is expressly disclaimed to the full extent permitted by the law.

This publication is provided as is, and is to be used at the recipient's own risk.

The recipient is advised to consider seeking professional guidance with respect to its use of this publication.

This publication is not intended to constitute a contract. Users are responsible for its correct application.

© The British Standards Institution 2021
Published by BSI Standards Limited 2021

ISBN 978 0 539 16791 7

ICS 83.060

Compliance with a British Standard cannot confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 31 July 2021.

Amendments/corrigenda issued since publication

Date	Text affected
------	---------------

INTERNATIONAL
STANDARD

ISO
6505

Fifth edition
2021-07-08

**Rubber, vulcanized or
thermoplastic — Determination
of tendency to adhere to and
corrode metals**

*Caoutchouc, vulcanisé ou thermoplastique — Détermination de la
tendance à adhérer aux métaux et à les corroder*



Reference number
ISO 6505:2021(E)



COPYRIGHT PROTECTED DOCUMENT

© ISO 2021, Published in Switzerland

All rights reserved. Unless otherwise specified, no part of this publication may be reproduced or utilized otherwise in any form or by any means, electronic or mechanical, including photocopying, or posting on the internet or an intranet, without prior written permission. Permission can be requested from either ISO at the address below or ISO’s member body in the country of the requester.

ISO copyright office
Ch. de Blandonnet 8 • CP 401
CH-1214 Vernier, Geneva, Switzerland
Tel. +41 22 749 01 11
Fax +41 22 749 09 47
copyright@iso.org
www.iso.org

Contents		Page
Foreword		iv
1	Scope	1
2	Normative references	1
3	Terms and definitions	1
4	Principle	1
5	Materials	2
6	Apparatus	2
7	Test metals	2
8	Calibration	4
9	Test pieces	4
9.1	Preparation	4
9.1.1	Square test pieces	4
9.1.2	O-ring test pieces	4
9.2	Number	4
9.3	Time-interval between forming the material and testing	4
9.4	Storage	4
10	Test conditions	4
10.1	Temperature	4
10.2	Test period	4
10.3	Humidity	4
11	Procedure	5
11.1	Precaution	5
11.2	Preparation of rubber test pieces for testing	5
11.3	Number of metal test strips	5
11.4	Preparation of surfaces of metal test strips	5
11.5	Determination	5
11.5.1	Tests in a dry atmosphere	5
11.5.2	Tests in a wet atmosphere	6
12	Expression of results	7
12.1	Degree of adhesion	7
12.2	Degree of corrosion	7
12.2.1	For tests in a dry atmosphere	7
12.2.2	For tests in a wet atmosphere	7
13	Test report	7
Annex A (normative) Calibration schedule		9
Annex B (informative) Grading of degree of corrosion		11

Foreword

ISO (the International Organization for Standardization) is a worldwide federation of national standards bodies (ISO member bodies). The work of preparing International Standards is normally carried out through ISO technical committees. Each member body interested in a subject for which a technical committee has been established has the right to be represented on that committee. International organizations, governmental and non-governmental, in liaison with ISO, also take part in the work. ISO collaborates closely with the International Electrotechnical Commission (IEC) on all matters of electrotechnical standardization.

The procedures used to develop this document and those intended for its further maintenance are described in the ISO/IEC Directives, Part 1. In particular, the different approval criteria needed for the different types of ISO documents should be noted. This document was drafted in accordance with the editorial rules of the ISO/IEC Directives, Part 2 (see www.iso.org/directives).

Attention is drawn to the possibility that some of the elements of this document may be the subject of patent rights. ISO shall not be held responsible for identifying any or all such patent rights. Details of any patent rights identified during the development of the document will be in the Introduction and/or on the ISO list of patent declarations received (see www.iso.org/patents).

Any trade name used in this document is information given for the convenience of users and does not constitute an endorsement.

For an explanation of the voluntary nature of standards, the meaning of ISO specific terms and expressions related to conformity assessment, as well as information about ISO's adherence to the World Trade Organization (WTO) principles in the Technical Barriers to Trade (TBT), see www.iso.org/iso/foreword.html.

This document was prepared by Technical Committee ISO/TC 45, *Rubber and rubber products*, Subcommittee SC 2, *Testing and analysis*.

This fifth edition cancels and replaces the fourth edition ([ISO 6505:2015](http://www.iso.org/iso/6505:2015)), of which it constitutes a minor revision. The main changes compared to the previous edition are as follows:

- the Introduction has been deleted;
- the Normative references in [Clause 2](#) have been updated.

Any feedback or questions on this document should be directed to the user's national standards body. A complete listing of these bodies can be found at www.iso.org/members.html.

Rubber, vulcanized or thermoplastic — Determination of tendency to adhere to and corrode metals

WARNING 1 — Persons using this document should be familiar with normal laboratory practice. This document does not purport to address all of the safety problems, if any, associated with its use. It is the responsibility of the user to establish appropriate safety and health practices and to determine the applicability of any other restrictions.

WARNING 2 — Certain procedures specified in this document might involve the use or generation of substances, or the generation of waste, that could constitute a local environmental hazard. Reference should be made to appropriate documentation on safe handling and disposal after use.

1 Scope

This document specifies a method for the determination of the tendency of vulcanized or thermoplastic rubbers to adhere to and to corrode metals when exposed to a specified test environment.

2 Normative references

The following documents are referred to in the text in such a way that some or all of their content constitutes requirements of this document. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

[ISO 48-2](#), *Rubber, vulcanized or thermoplastic — Determination of hardness — Part 2: Hardness between 10 IRHD and 100 IRHD*

[ISO 3310-1](#), *Test sieves — Technical requirements and testing — Part 1: Test sieves of metal wire cloth*

[ISO 18899:2013](#), *Rubber — Guide to the calibration of test equipment*

[ISO 23529](#), *Rubber — General procedures for preparing and conditioning test pieces for physical test methods*

3 Terms and definitions

No terms and definitions are listed in this document.

ISO and IEC maintain terminological databases for use in standardization at the following addresses:


- ISO Online browsing platform: available at <https://www.iso.org/obp>
- IEC Electropedia: available at <http://www.electropedia.org/>

4 Principle

Rubber test pieces are held between metal test strips under specified conditions in a dry or wet atmosphere for a specified period.

Subsequent visual examination of the metal surface provides a subjective indication of the degree of adhesion to the metal by the rubber and corrosion of the metal.

Dimensions in millimetres

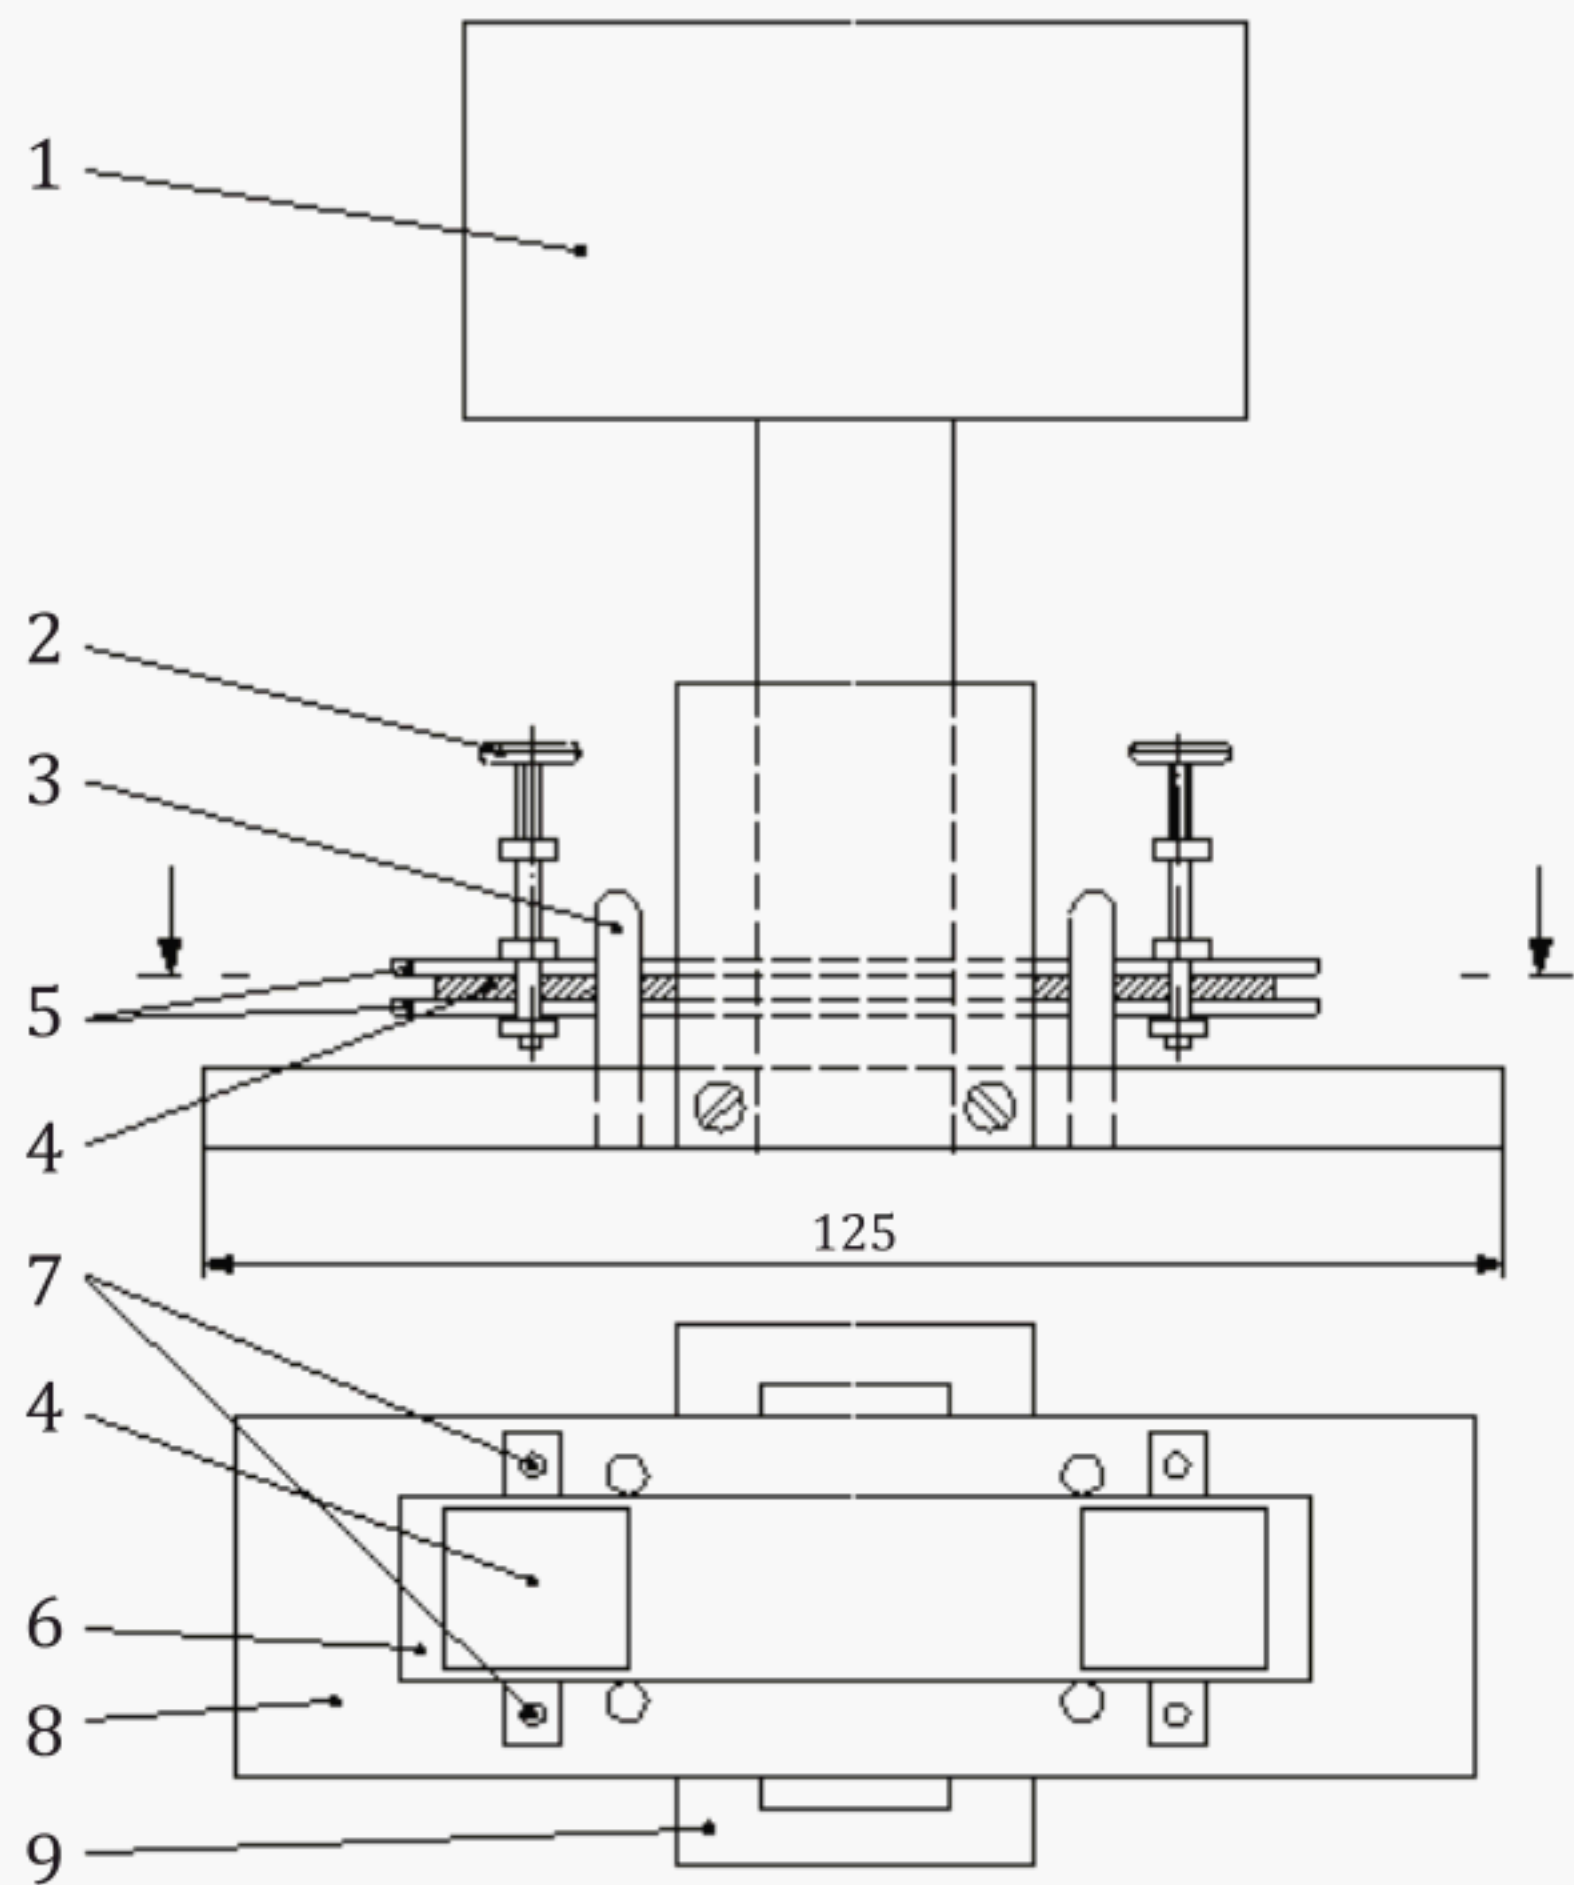

Key

- | | | | | | |
|---|--------------|---|-------------------------|---|-------------------------|
| 1 | 10 kg weight | 4 | rubber test piece | 7 | positions of clamps |
| 2 | screw clamp | 5 | metal test strips | 8 | support base |
| 3 | locating pin | 6 | bottom metal test strip | 9 | guides for 10 kg weight |

Figure 1 — Typical support jig

The metal test strips shall have a thickness sufficient to withstand the clamping force without bending. If only thin foil is available, it shall be supported by a rigid backing material previously shown to be non-corrosive to the test metals.

The test metals shall be in the form of strips with dimensions as given in [Table 1](#).

Table 1 — Dimensions of metal test strips

Width mm	Length (min.) mm	Comments
25 ± 1	100	For use with square test pieces measuring 20 mm × 20 mm
50 ± 1	100	For use with O-rings with an outer diameter of 18 mm to 45 mm

8 Calibration

The requirements for calibration of the test apparatus are given in [Annex A](#).

9 Test pieces

9.1 Preparation

9.1.1 Square test pieces

Square test pieces shall be $(20 \pm 0,5)$ mm \times $(20 \pm 0,5)$ mm and preferably with a thickness of $(2,0 \pm 0,2)$ mm. They shall be cut or punched from sheet or from the product under evaluation in accordance with [ISO 23529](#).

9.1.2 O-ring test pieces

O-ring test pieces shall have a cross-sectional diameter of $(3,55 \pm 0,1)$ mm. The outer diameter of the test piece shall be min. 18 mm and max. 45 mm.

9.2 Number

At least two test pieces shall be used for each test.

9.3 Time-interval between forming the material and testing

The time-interval between forming the material and testing shall be in accordance with [ISO 23529](#).

9.4 Storage

Samples and test pieces shall be protected from light as completely as possible during the interval between forming and testing.

10 Test conditions

10.1 Temperature

The test temperature shall be selected from the list in [ISO 23529](#).

10.2 Test period

The duration of the test shall be selected from the following: 24_{-2}^0 h; 72_{-2}^0 h; (96 ± 2) h; (120 ± 2) h; (168 ± 2) h and multiples of 7 days.

NOTE The test period of 120 h has been included alongside periods from [ISO 23529](#) because it is used in material specifications, especially for testing in a wet atmosphere.

10.3 Humidity

In terms of humidity, the atmosphere shall be

- a) either a dry atmosphere having a relative humidity of less than 10 %, or
- b) a wet atmosphere having a relative humidity of (90 ± 5) %.

NOTE This test is commonly carried out at low humidity to ensure that corrosion resulting from causes other than those due to the rubber is minimized.

11 Procedure

11.1 Precaution

In all operations, it is essential that the rubber test pieces and the metal test strips are handled only by means of the polyethylene gloves or other protective equipment (see [6.4](#)). This precaution is essential in order to minimize surface contamination of the test piece and metal strips.

11.2 Preparation of rubber test pieces for testing

Clean all the surfaces of the rubber test pieces with cotton wool pads moistened with a suitable solvent (see [5.2](#)) to remove surface contamination (by mould release agents, for example). The solvent to be used will depend on the rubber under test; it shall not have any deleterious effects on the rubber (e.g. acetone should not be used for nitrile rubber; isopropyl alcohol is preferred for this material).

Allow the test pieces to dry in air. When dry, store the test pieces, unless otherwise specified, in a clean desiccator over silica gel at standard laboratory temperature (see [ISO 23529](#)) for at least 24 h immediately prior to testing.

Since cleaning of the test pieces might also remove from the rubber surface materials such as waxes, antiozonants, etc., which would normally be expected to affect the adhesion and corrosion properties of the rubber, allow sufficient time in the desiccator for the re-formation of the “original” surface before testing.

11.3 Number of metal test strips

For each test, use two suitable metal test strips as specified in the material specification or selected from the metals specified in [Clause 7](#).

For tests in a wet atmosphere, use only one type of metal in the construction of the test piece “sandwich” in order to avoid electrolytic effects.

11.4 Preparation of surfaces of metal test strips

Thoroughly scour the test surfaces of the metal test strips using a slurry of pumice powder ([5.3](#)) in water applied with a cotton wool pad until a matt surface is obtained. Thoroughly rinse the metal strips with water ([5.4](#)) and then with acetone ([5.1](#)) and finally dry in air. If the prepared metal test strips are not to be used immediately after cleaning, store them in a clean desiccator over silica gel for not more than 24 h before testing.

11.5 Determination

11.5.1 Tests in a dry atmosphere

11.5.1.1 Tests using sheet material (square test pieces)

Take two rubber test pieces as specified in [9.1.1](#), prepared as specified in [11.2](#), and two metal strips of dimensions 25 mm by 100 mm, prepared as specified in [11.4](#). Place the two pieces of rubber between the prepared surfaces of the metal strips so that they are approximately 40 mm apart and equidistant from the ends (see [Figure 1](#)). Align the rubber/metal sandwich so formed in the support jig and apply a $(10 \pm 0,1)$ kg weight (equivalent to 122,5 kPa acting on the rubber) to the test piece sandwich. Tighten the two screws, one at each end of the sandwich, with just sufficient force to maintain the clamping force when the 10 kg weight is removed. Remove the 10 kg weight from the jig, place the sandwich in the test chamber ([6.3](#)) and maintain it at the test temperature for the test period (see [Clause 10](#)).

At the end of the test period, remove the sandwich from the test chamber, allow to cool, if appropriate, to standard laboratory temperature and maintain it at this temperature for at least 1 h. Release the

screw clamps and carefully separate the metal strips from the rubber test pieces. Examine the surface of the metal previously in contact with the rubber for signs of adhesion and corrosion. Use a magnifying glass (6.5) in examining for corrosion.

11.5.1.2 Tests using O-rings

Take two O-rings of the same size, as specified in 9.1.2, prepared as specified in 11.2, and two metal strips of dimensions 50 mm by 100 mm, prepared as specified in 11.4. Place the O-rings between the prepared surfaces of the metal strips so that they are approximately 40 mm apart and approximately equidistant from the ends of the metal strips. Align the metal/rubber sandwich so formed in the support jig and apply a load L in accordance with Table 2 to the test piece sandwich. Tighten the two screw clamps, one at each end of the sandwich, with just sufficient force to maintain the clamping force when the load is removed. Remove the load from the jig, place the sandwich in the test chamber (6.3) and maintain it at the test temperature for the test period (see Clause 10).

At the end of the test period, remove the sandwich from the test chamber, allow to cool, if appropriate, to standard laboratory temperature and maintain it at this temperature for at least 1 h. Release the screw clamps and carefully separate the metal strips from the rubber O-rings. Examine the surface of the metal previously in contact with the rubber for signs of adhesion and corrosion. Use a magnifying glass (6.5) in examining for corrosion.

11.5.2 Tests in a wet atmosphere

11.5.2.1 Tests using sheet material (square test pieces)

Take two rubber test pieces as specified in 9.1.1, prepared as specified in 11.2, and two metal strips of dimensions 50 mm by 100 mm, prepared as specified in 11.4. Place the two pieces of rubber between the prepared surfaces of the metal strips so that they are approximately 40 mm apart and equidistant from the ends (see Figure 1). Align the rubber/metal sandwich so formed in the support jig and apply a $(10 \pm 0,1)$ kg weight (equivalent to 122,5 kPa acting on the rubber) to the test piece sandwich. Tighten the two screws, one at each end of the sandwich, with just sufficient force to maintain the clamping force when the 10 kg weight is removed. Remove the 10 kg weight from the jig, place the sandwich in the test chamber (6.3) and maintain it at the standard laboratory temperature and a relative humidity of (90 ± 5) % for the test period (see 10.2).

At the end of the test period, remove the sandwich from the test chamber, release the screw clamps and carefully separate the metal strips from the rubber test pieces. Keep the metal strips in an atmosphere at standard laboratory temperature and a relative humidity of (50 ± 5) % for 16 h to 24 h. At the end of this period, examine the surface of the metal previously in contact with the rubber for signs of adhesion and corrosion. Use a magnifying glass (6.5) in examining for corrosion.

11.5.2.2 Tests using O-rings

Take two O-rings of the same size, as specified in 9.1.2, prepared as specified in 11.2, and two metal strips of dimensions 50 mm by 100 mm, prepared as specified in 11.4. Place the O-rings between the prepared surfaces of the metal strips so that they are approximately 40 mm apart and approximately equidistant from the ends of the metal strips. Align the metal/rubber sandwich so formed in the support jig and apply a load L in accordance with Table 2 to the test piece sandwich. Tighten the two screw clamps, one at each end of the sandwich, with just sufficient force to maintain the clamping force when the load is removed. Remove the load from the jig and place the sandwich in the test chamber (6.3) and maintain it at the standard laboratory temperature and a relative humidity of (90 ± 5) % for the test period (see 10.2).

At the end of the test period, remove the sandwich from the test chamber, release the screw clamps and carefully separate the metal strips from the rubber O-rings. Keep the metal strips in an atmosphere at standard laboratory temperature and a relative humidity of (50 ± 5) % for 16 h to 24 h. At the end of this period, examine the surface of the metal previously in contact with the rubber for signs of adhesion and corrosion. Use a magnifying glass (6.5) in examining for corrosion.

Table 2 — Choice of test load

Rubber hardness determined in accordance with ISO 48-2 IRHD	Load per mm circumference ΔL N/mm	The load L required is calculated, in newtons, from the formula $L=2\times\Delta L\times\pi(D_i+d)$ where ΔL is the inner circumference in N/mm; D_i is the inner diameter of the O-ring in mm; D is the inner thickness of the O-ring in mm; 2 allows for the fact that the load is spread over two pieces.
50	0,4 ± 0,05	
55	0,5 ± 0,05	
60	0,6 ± 0,05	
65	0,8 ± 0,05	
70	1,1 ± 0,05	
75	1,5 ± 0,1	
80	1,9 ± 0,1	
85	2,6 ± 0,2	
90	3,3 ± 0,2	

12 Expression of results

12.1 Degree of adhesion

Evaluate the degree of adhesion in accordance with the following criteria.

- a) Complete separation of rubber from both metal surfaces. No indication of any adhesion.
- b) Considerable force necessary to separate the metal surfaces. Particles of rubber remain adhering to one or both metal surfaces.

12.2 Degree of corrosion

Evaluate the degree of corrosion in accordance with the following criteria.

12.2.1 For tests in a dry atmosphere

- a) no surface stain or corrosion;
- b) surfaces stained or discolouration present, but no corrosion as evidenced by pitting or erosion of one or both metal surfaces;
- c) corrosion as evidenced by pitting and erosion on one or both metal surfaces.

12.2.2 For tests in a wet atmosphere

For that part of the metal strip which has been in contact with the test piece, the degree of corrosion shall be graded from 0 to 5 where 0 is no staining or corrosion and 5 is severe staining or corrosion. Examples of grades 1 to 5 are given for O-ring test pieces in [Annex B](#).

13 Test report

The test report shall include the following information:

- a) sample details:
 - 1) full description of the sample and its origin;

- 2) method of preparation of test piece from the sample, for example moulded or cut;
- b) test method:
 - 1) a full reference to the test method used, i.e. the number of this document, i.e. [ISO 6505](#);
 - 2) the test procedure used;
- c) test details:
 - 1) details of the metal(s) used;
 - 2) the laboratory temperature;
 - 3) the time and temperature of conditioning prior to test;
 - 4) the temperature of test, if other than standard laboratory temperature and the relative humidity if necessary;
 - 5) the test duration;
 - 6) details of any procedures not specified in this document;
- d) test results
 - 1) the number of test pieces used;
 - 2) test results: details of any adhesion and/or corrosion;
- e) date(s) of test.

Annex A

(normative)

Calibration schedule

A.1 Inspection

Before any calibration is undertaken, the condition of the items of apparatus to be calibrated shall be ascertained by inspection and recorded in a calibration report or certificate. It shall be reported whether calibration is made in the “as-received” condition or after rectification of any abnormality or fault.

It shall be ascertained whether the apparatus is, in general, fit for the intended purpose, including any parameters specified as approximate and for which the apparatus does not therefore need to be formally calibrated. If such parameters are liable to change, then the need for periodic checks shall be written into the detailed calibration procedures.

A.2 Calibration schedule

For each item, the calibration procedure is indicated in the schedule given in [Table A.1](#) by the code-letter C (indicating that confirmation is necessary that the requirement is met, but no measurement is necessary) or by reference to a clause or subclause in [ISO 18899](#).

The verification frequency for each item is given in [Table A.1](#) by the following code-letters:

- N initial verification only;
- S verification at the standard interval given in [ISO 18899](#);
- U verification in use.

Table A.1 — Calibration schedule

Item	Requirement	Procedure	Verification frequency	Notes
Support jig	Capable of withstanding the clamping force throughout the test	C	N	
Test chamber	As per ISO 23529			
Temperature control	As per ISO 23529	ISO 18899 :2013, Clause 18	S	
Magnification glass	×3 to ×5	C	N	
Test metal strip material				
Size of test metal strip	25 mm or 50 mm wide by ≥100 mm long	C	N	
Thickness of strip	Sufficient to withstand the clamping force	C	U	
if made of thin foil	Use non-corrosive rigid backing material	C	U	
Humidity	<10 % or 90 %	ISO 18899 :2013, Clause 20	S	
If high humidity used	Use like metals in sandwich	C	U	

Item	Requirement	Procedure	Verification frequency	Notes
Preparation of rubber	Clean all surfaces with a suitable solvent having no deleterious effect on the rubber. Handle with gloves or similar.	C	U	e.g. do not use acetone on nitrile rubber
Storage	In clean desiccator over silica gel, protected from light	C	U	
Distance apart of two rubber test pieces	Approximately 40 mm	C	U	
Test load (tests on O-rings)	See Table 2	ISO 18899 :2013, 21.3	S	
Applied weight (tests on square test pieces)	(10 ± 0,1) kg	ISO 18899 :2013, 22.2		
Relative humidity	(90 ± 5) %	ISO 18899 :2013, Clause 20	S	
Materials	Acetone of analytical quality Solvents of analytical quality (having no deleterious effect on the rubber under test) Pumice powder, passing through a sieve of nominal aperture size 53 µm complying with ISO 3310-1 Distilled water or water of equivalent purity Silica gel Polyethylene or polypropylene medical gloves or forceps			

In addition to the items listed in [Table A.1](#), use of the following items is implied, all of which will need calibrating in accordance with [ISO 18899](#):

- a timer;
- a thermometer for monitoring the conditioning temperature;
- instruments for determining the length, width and thickness of the test pieces.

Annex B
(informative)

Grading of degree of corrosion



Grade 1




Grade 2



Grade 3



Grade 4

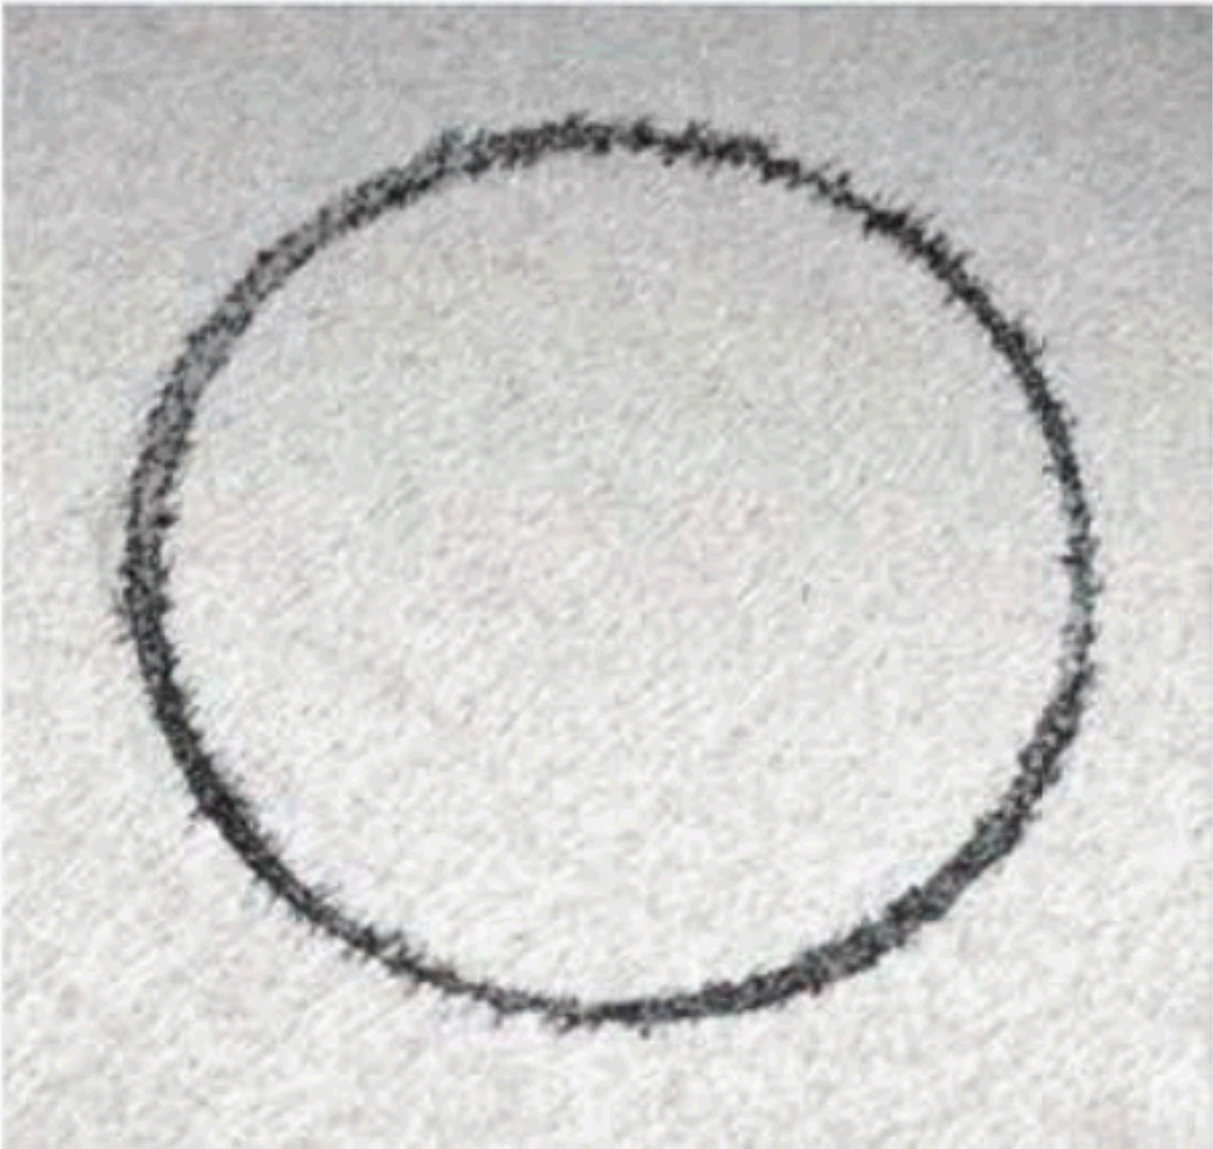

Grade 5

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Copyright in BSI publications

All the content in BSI publications, including British Standards, is the property of and copyrighted by BSI or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use.

Save for the provisions below, you may not transfer, share or disseminate any portion of the standard to any other person. You may not adapt, distribute, commercially exploit or publicly display the standard or any portion thereof in any manner whatsoever without BSI's prior written consent.

Storing and using standards

Standards purchased in soft copy format:

- A British Standard purchased in soft copy format is licensed to a sole named user for personal or internal company use only.
- The standard may be stored on more than one device provided that it is accessible by the sole named user only and that only one copy is accessed at any one time.
- A single paper copy may be printed for personal or internal company use only.

Standards purchased in hard copy format:

- A British Standard purchased in hard copy format is for personal or internal company use only.
- It may not be further reproduced – in any format – to create an additional copy. This includes scanning of the document.

If you need more than one copy of the document, or if you wish to share the document on an internal network, you can save money by choosing a subscription product (see 'Subscriptions').

Reproducing extracts

For permission to reproduce content from BSI publications contact the BSI Copyright and Licensing team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email cservices@bsigroup.com.

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Useful Contacts

Customer Services

Tel: +44 345 086 9001

Email: cservices@bsigroup.com

Subscriptions

Tel: +44 345 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

